

TCAL6: TCS Al-based Alloy Database

<i>Database name:</i>	TCS Al-based Alloys Database	<i>Database acronym:</i>	TCAL
<i>Database owner:</i>	Thermo-Calc Software AB	<i>Database version:</i>	6.0

TCAL6 is a thermodynamic database for Al-based alloys for use with Thermo-Calc and the add-on Diffusion Module (DICTRA) and/or Precipitation Module (TC-PRISMA). TCAL6 is based on the critical evaluation of binary, ternary and important higher-order systems which enables predictions to be made for multi-component systems and alloys of industrial importance.

A hybrid approach of experiments, first-principles calculations and CALPHAD modeling has been used to obtain thermodynamic descriptions of the constituent binary and ternary systems over the whole composition and temperature ranges. The TCAL6 database is validated where possible against higher-order systems and is the result of a long-term collaboration with academia that has involved extensive experimental work, theoretical calculations and critical assessments of the published literature.

Included Elements (36)

The database has been developed in a 36 element framework:

Al	Ag	B	Be	Bi	C	Ca	Cd	Ce	Co
Cr	Cu	Er	Fe	Ga	Ge	H	Hf	In	K
La	Li	Mg	Mn	Mo	Na	Ni	Pb	Sc	Si
Sn	Sr	Ti	V	Zn	Zr				

In total, 260 of the binary systems have been assessed, mostly to their full range of composition, and can be calculated with the BINARY Module in Thermo-Calc. TCAL6 also contains assessments of 88 ternaries, and these can be calculated with the TERNARY Module in Thermo-Calc. Many quaternaries with Al as one element have also been assessed.

TCAL6 contains nearly 600 solution and intermetallic phases in total. The GAS phase is rejected by default when retrieving the data from the database. When this phase is required for a calculation, it has to be manually restored. Phase diagrams of assessed binary and ternary systems can be conducted using the BINARY and TERNARY modules, respectively.

▶ [TCAL6 Included Phases](#)

▶ [TCAL6 Models for the Included Phases](#)

TCAL6 includes nearly all stable phases in the assessed systems and most important metastable phases (or precipitates) that may form in as-cast and aged Al-based alloys. The database can be used to calculate various phase diagrams and property diagrams in the assessed systems or even extrapolated higher-order systems. The extrapolation to higher-order systems helps to understand the phase equilibria in multi-component industrial aluminum alloys to be able to predict the phase formation, phase fractions and phase compositions or to calculate the driving force of forming a phase. Note that the extrapolation to higher-order systems might not be valid beyond the Al-rich region. The database can also be used for predicting solidification behaviour of Al-alloys with the SCHEIL_GULLIVER module in Thermo-Calc and simulating multi-particle precipitation during aging treatment with the add-on Precipitation Module (TC-PRISMA).

Some ordered compounds with the structure of $L1_2$ or B2 were modeled as stoichiometric phases, and named as L12_FCC and B2_BCC, respectively. The $L1_2$ -type precipitate that forms in Er, Li and Sc containing aluminum alloys was modeled as Al₃X, and its solubility of Ti, Zr and Mg was described. In general, however, the B2 phase, together with the bcc_A2 phase, has been modeled with the so-called partition model, which describes an ordered phase and its disordered counterpart using a single Gibbs energy curve. This type of description is of particular importance to be able to predict second order transformations between a disordered phase and its ordered structures. The fcc_A1 solid solution phase, including the (Al) matrix phase in aluminum alloys, is treated independently with the substitutional model.



In Console Mode, you can list phases and constituents in the Database module and the GES module. For some phases, supplementary information is included in the definitions. In order to show the information, it is recommended to use “List-System” with the option of “Constituents” in the Database module.

Database Revision History

If you are interested in the revision history for this database, the information is available in the online help (from Thermo-Calc go to **Help>Online Help**) or in the release notes on our [website](#).

TCAL6 Assessed Binary Systems

These are the assessed binary systems, which are mostly in the full range of composition and temperature.

	Al	Ag	B	Be	Bi	C	Ca	Ce	Cd	Co	Cr	Cu	Er	Fe	Ga	Ge	H	Hf	In	K	La	Li	Mg	Mn	Mo	Na	Ni	Pb	Sc	Si	Sn	Sr	Ti	V	Zn	Zr		
Ag	2																																					
B		2																																				
Be				2																																		
Bi					2																																	
C			2			2																																
Ca	2						2																															
Ce								2																														
Cd									2																													
Co										2																												
Cr			2			2		2			2																											
Cu	2	2			2	2	2	2	2	2	2	2																										
Er	2											2	2																									
Fe	2	2				2	2	2			2	2	2	2																								
Ga												2			2																							
Ge			2								2	2		2		2																						
H						2						2		2			2																					
Hf												2		2				2																				
In												2							2																			
K														2			2	2			2																	
La	2						2					2		2				2				2																
Li	2									2	2	2		2			2	2			2		2															
Mg	2	2				2		2			2	2	2	2		2	2	2	2		2		2	2														
Mn	2	2				2	2	2			2	2		2		2	2	2			2	2	2	2		2												
Mo																									2													
Na	2						2					2		2				2	2		2		2			2												
Ni	2	2				2	2	2			2	2		2		2	2	2	2			2	2	2	2			2										
Pb												2																	2									
Sc	2						2					2		2				2				2	2		2		2	2		2								
Si	2	2	2			2	2	2			2	2	2	2		2		2			2	2	2	2	2	2	2	2		2	2							
Sn		2			2	2			2		2	2		2		2			2				2	2				2	2		2	2						
Sr		2				2	2				2	2		2			2							2	2			2			2	2	2					
Ti		2				2					2	2		2			2						2	2			2			2	2	2	2	2				
V		2				2					2	2		2			2						2	2			2				2	2	2	2	2			
Zn	2	2				2	2				2	2		2		2	2			2	2	2	2	2		2	2			2	2	2	2	2	2	2		
Zr		2				2					2	2	2	2		2						2	2	2				2		2	2	2	2	2	2	2	2	

TCAL6 Assessed Ternary Systems

These are the assessed ternary systems, which are mostly in full compositional ranges.

Al-Ag-Cu
Al-Bi-Sn
Al-C-Si
Al-Cd-Sn
Al-Ce-Cr
Al-Ce-Cu
Al-Ce-Fe
Al-Ce-Mg
Al-Ce-Mn
Al-Ce-Ni
Al-Ce-Si
Al-Cr-Si
Al-Cr-Sn
Al-Cu-Er
Al-Cu-Fe
Al-Cu-Li
Al-Cu-Mg
Al-Cu-Mn
Al-Cu-Ni

Al-Cu-Sc
Al-Cu-Si
Al-Cu-Sn
Al-Cu-Zn
Al-Er-Fe
Al-Er-Mg
Al-Fe-Mg
Al-Fe-Mn
Al-Fe-Ni
Al-Fe-Si
Al-Fe-Zn
Al-In-Sn
Al-Li-Mg
Al-Li-Si
Al-Li-Zr
Al-Mg-Mn
Al-Mg-Ni
Al-Mg-Si
Al-Mg-Zn
Al-Mn-Ni
Al-Mn-Si
Al-Mn-Zn
Al-Mo-Si
Al-Ni-Si

Al-Ni-Zn
Al-Sc-Si
Al-Sc-Ti
Al-Sc-Zr
Al-Si-Ti
Al-Si-Zn
Al-Sn-Pb
Al-Sn-Si
Al-Sn-Zn
Cu-Fe-Mg
Cu-Fe-Mn
Cu-Fe-Ni
Cu-Fe-Si
Cu-Fe-Zn
Cu-Li-Mg
Cu-Mg-Mn
Cu-Mg-Ni
Cu-Mg-Si
Cu-Mg-Zn
Cu-Mn-Ni
Cu-Mn-Si
Cu-Mn-Zn
Cu-Ni-Si
Cu-Ni-Zn

Cu-Si-Zn
Fe-Mg-Mn
Fe-Mg-Ni
Fe-Mg-Si
Fe-Mg-Zn
Fe-Mn-Ni
Fe-Mn-Si
Fe-Mn-Zn
Fe-Ni-Si
Fe-Ni-Zn
Fe-Si-Zn
Mg-Mn-Ni
Mg-Mn-Si
Mg-Mn-Zn
Mg-Ni-Si
Mg-Ni-Zn
Mg-Si-Zn
Mn-Ni-Si
Mn-Ni-Zn
Mn-Si-Zn
Ni-Si-Zn

TCAL6 Assessed Quaternary Systems

Al-Cu-Fe-Mn
Al-Cu-Fe-Ni
Al-Cu-Mg-Ni
Al-Cu-Mg-Si
Al-Cu-Mg-Zn
Al-Cu-Mn-Si
Al-Cu-Ni-Si
Al-Fe-Mg-Mn
Al-Fe-Mg-Si
Al-Fe-Mn-Si
Al-Fe-Ni-Si
Al-Mg-Mn-Si

TCAL6 Calculation Examples



Phase diagrams shown have been calculated with various versions of the TCAL database, so small differences might be observed if they are recalculated with TCAL6. For the systems, which have been considerably or significantly improved, however, their phase diagrams should have already been updated.

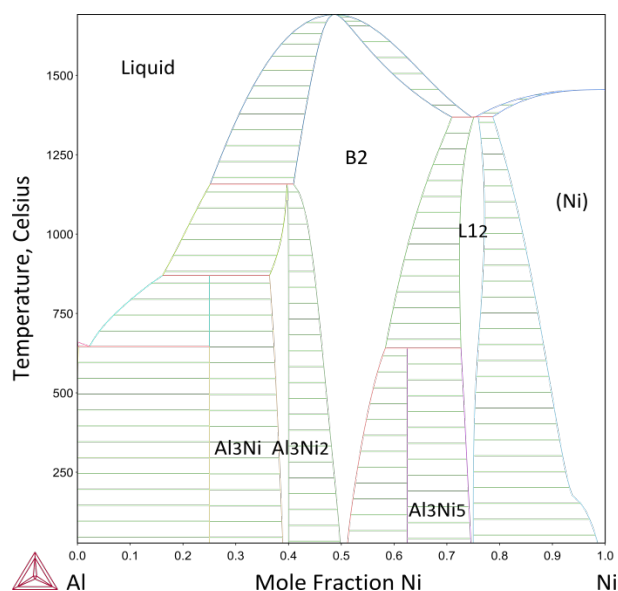


Figure 1: Calculated Al-Ni phase diagram [Ansara et al., 1997].

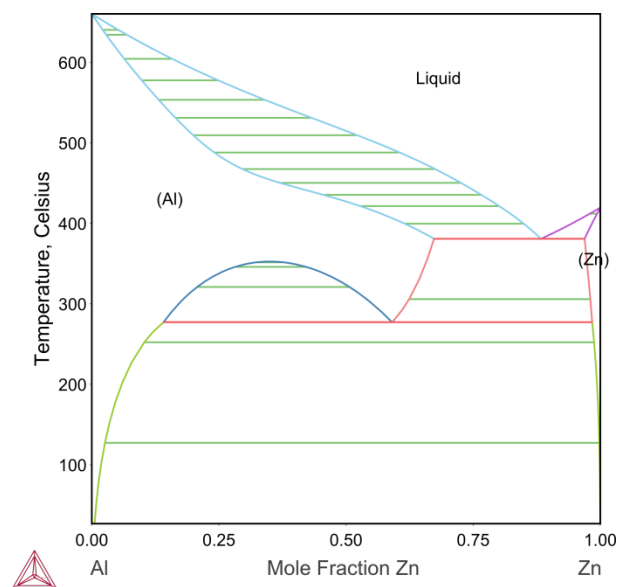


Figure 2: Calculated Al-Zn phase diagram [an Mey, 1993].

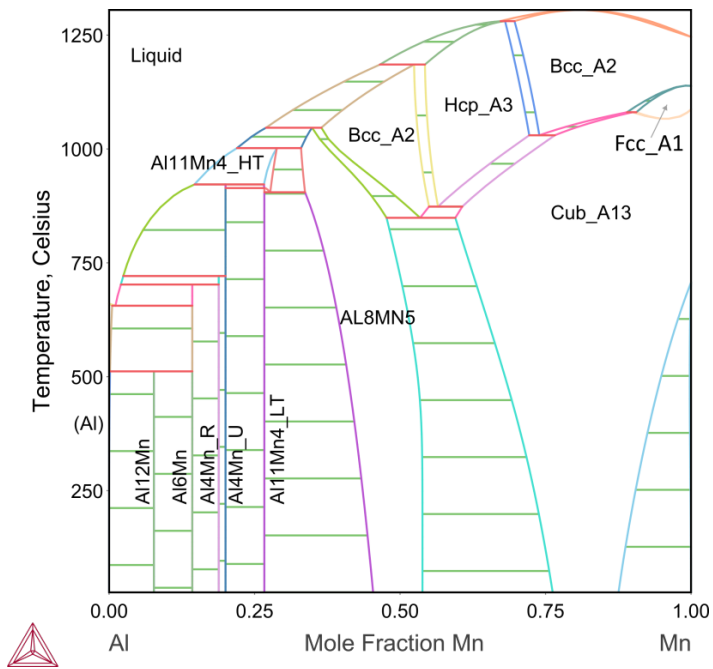


Figure 3: Calculated Al-Mn phase diagram [Du et al, 2007].

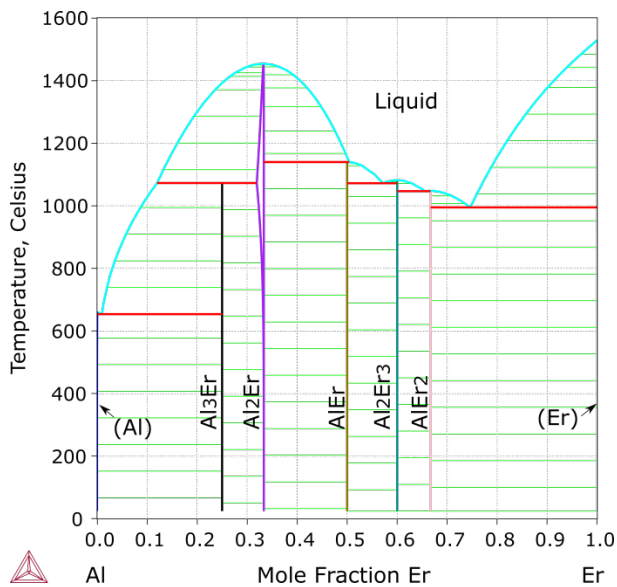


Figure 4: Calculated Al-Er phase diagram, where the Er solubility in (Al) was evaluated [Chen, 2017a].

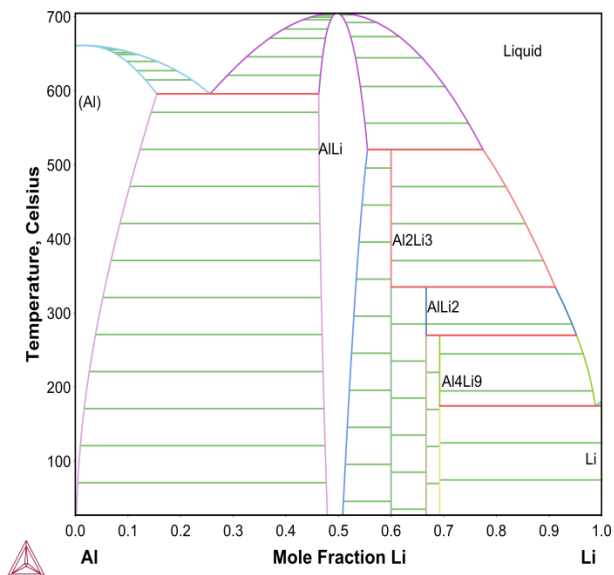


Figure 5: Calculated Al-Li phase diagram [Saunders, 1989 and Chen, 2012/2017b].

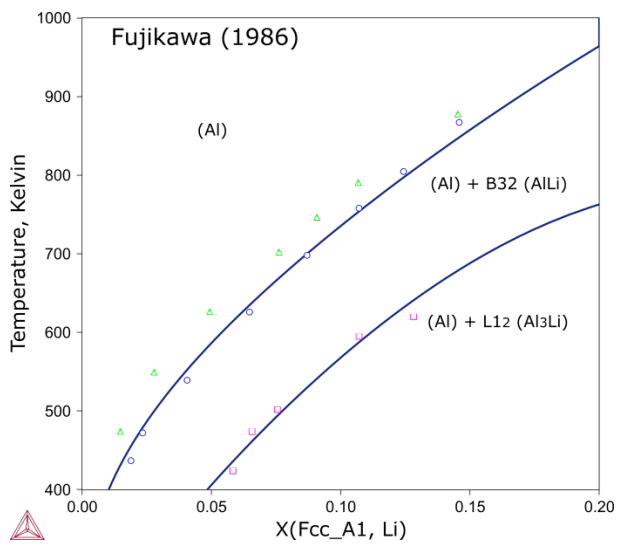


Figure 6: Calculated (Al) solvi in the Al-Li system [Saunders, 1989 and Chen, 2012/2017b], in comparison with the data from Fujikawa [1986].

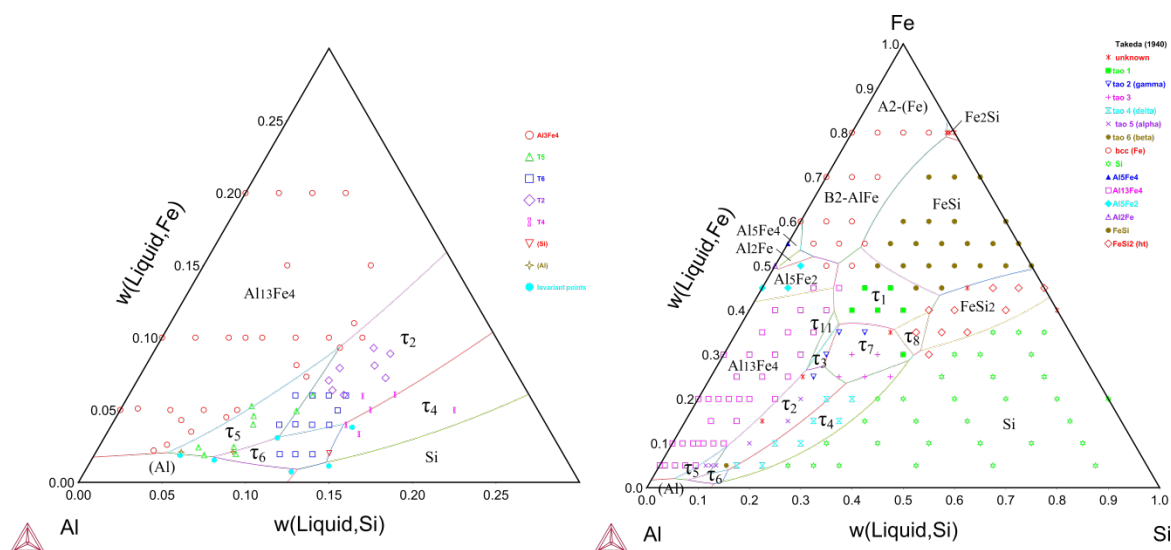


Figure 7: Calculated Al-Fe-Si liquidus projection (τ_5 : α -AlFeSi; τ_6 : β -AlFeSi), (a) in the Al-rich corner The invariant points are from Pontevichi et al. [2004] and Bosselet et al [2004]. The remaining data from Takeda and Mutuzaki [1940], Munson [1967] and Zakharov et al. [1988]; (b) over the entire compositional range, with the data from Takeda and Mutuzaki [1940].

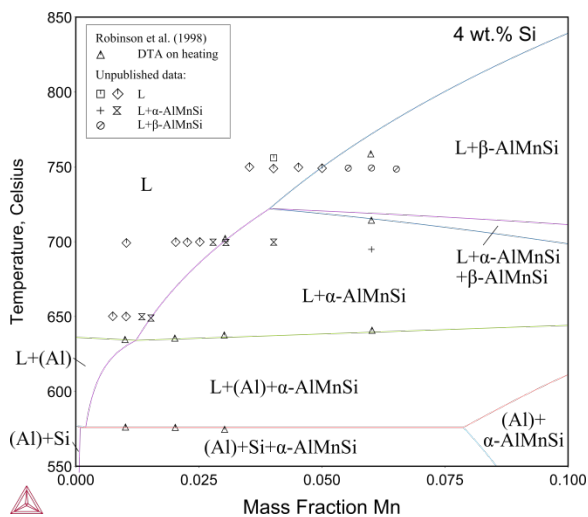


Figure 8: Al-Mn-Si vertical section at 4 wt. % Si (β -AlMnSi: τ_8 ; α -AlMnSi: τ_9) [Chen et al, 2014].

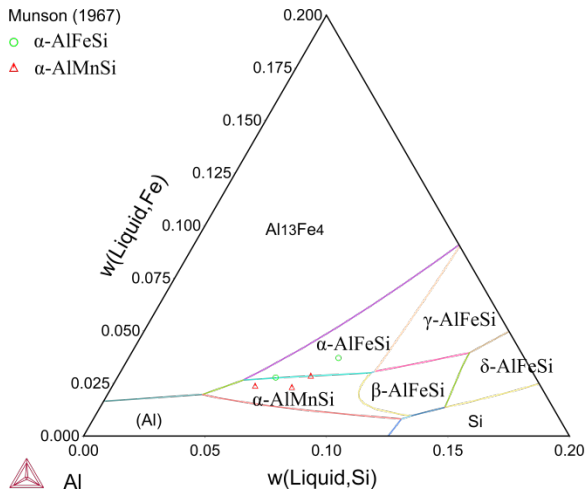


Figure 9: Al-Fe-Mn-Si liquidus surface at 0.3 wt. % Mn. (α -AlFeSi: τ_5 ; β -AlFeSi: τ_6 ; γ -AlFeSi: τ_2 ; δ -AlFeSi: τ_4 ; α -AlMnSi: τ_9) [Chen et al, 2014a].

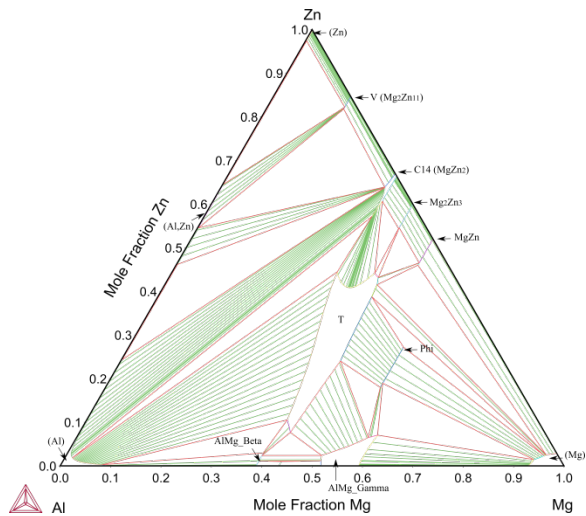


Figure 10: Isothermal section of Al-Mg-Zn at 335 °C [Liang et al., 1998].

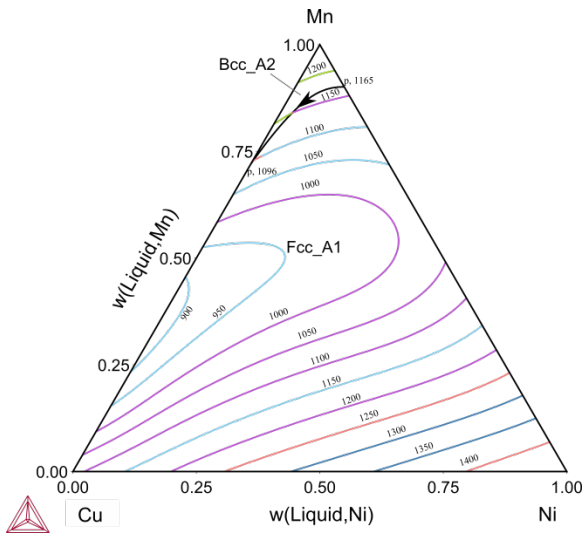


Figure 11: Liquidus projection with isothermal lines in the Cu–Mn–Ni system [Sun et al., 2009].

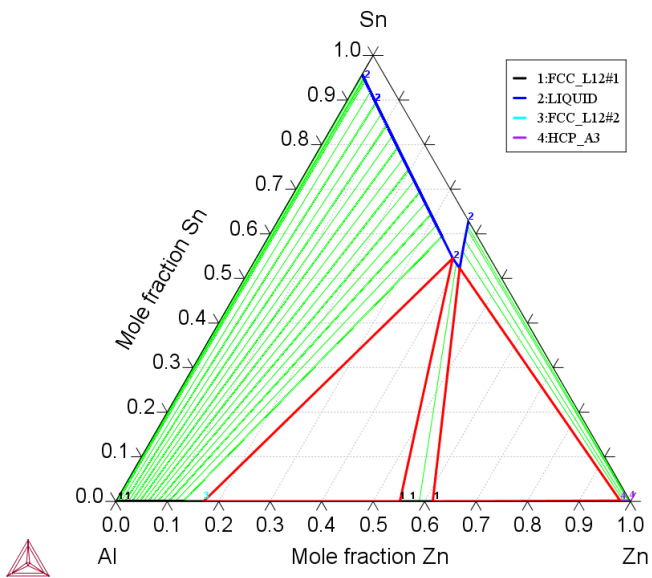


Figure 12: Al–Sn–Zn isothermal section at 300°C [Chen, 2017c].

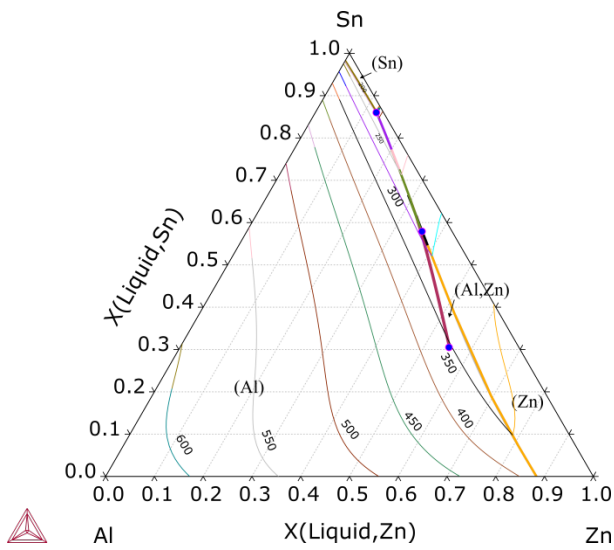


Figure 13: Al-Sn-Zn Liquidus surface projection with isotherms [Chen, 2017c].

Calculation: This work

■ ■ Schmid-Fetzer (1993)

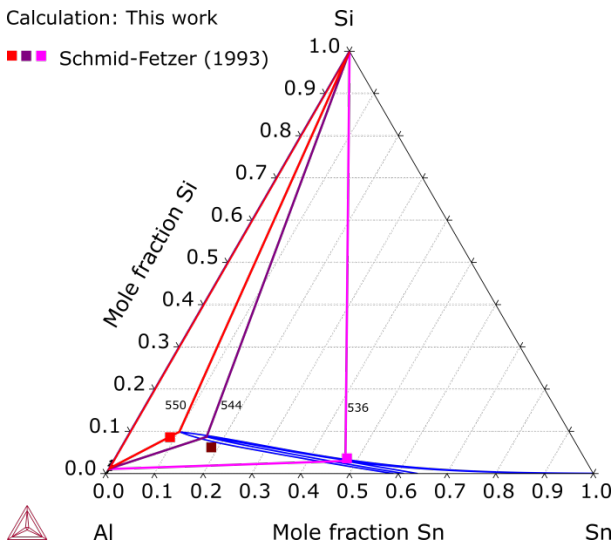


Figure 14: Calculated Al-Si-Sn isothermal sections at 536 °C, 544 °C and 550 °C [Chen, 2017c], with data read from Schmid-Fetzer [1993].

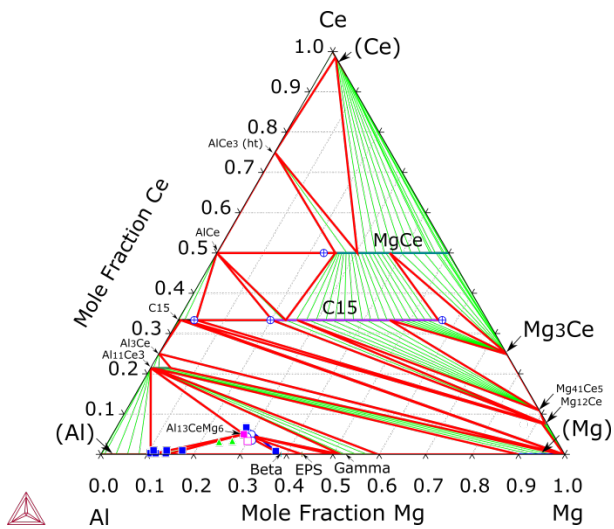


Figure 15: Al-Ce-Mg isothermal section at 400 °C [Chen, 2017d].

Al-Si-Mo at T=823.15 K

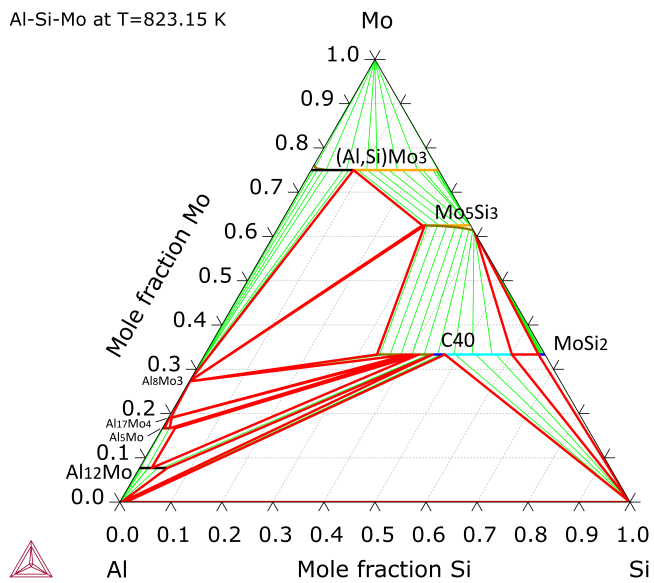


Figure 16: Al-Mo-Si isothermal section at 550 °C [2012, Guo].

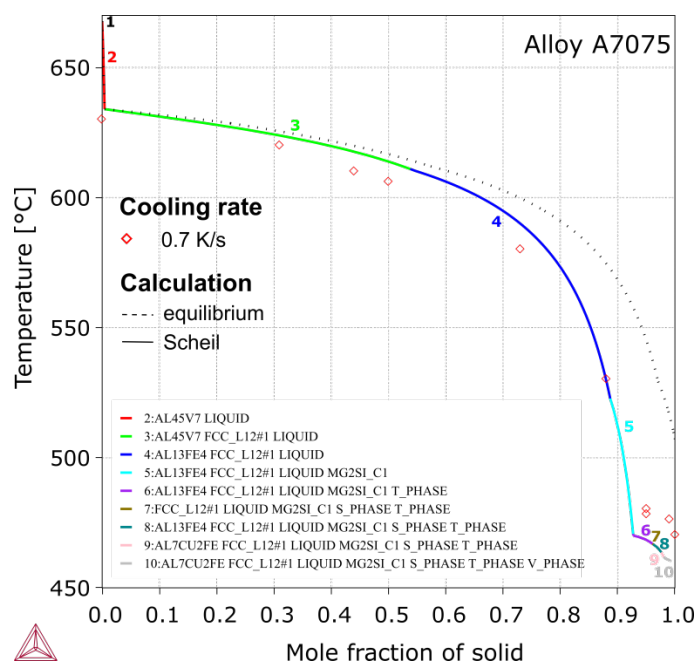


Figure 17: Equilibrium solidification and Scheil solidification simulations of alloy AA7075, compared with experimental results [Backerud, et al., 1990]. (Al), $Al_{13}Fe_4$, Mg_2Si , T-Phase and V-Phase ($MgZn_2$) are found in the microstructure as predicted from the calculation. $Al_{45}Cr_7$ forms primarily as a Cr-bearing phase, which may have been overlooked in experimental investigation due to its small amount. S-Phase was shown at the late stage of the Scheil solidification and its amount is small. Al_2Cu was experimentally observed but not shown in the calculation.

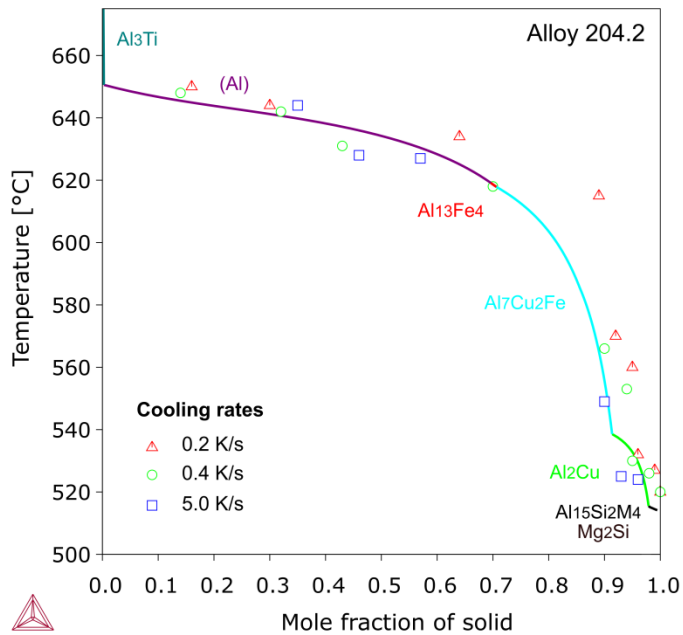


Figure 18: Scheil solidification simulation of foundry alloy 204.2 ($\text{Al-Si}_{0.08}\text{Fe}_{0.20}\text{Cu}_{4.40}\text{Mn}_{0.02}\text{Mg}_{0.22}\text{Ti}_{0.22}$, wt.%), compared with DTA experimental results [Backerud, et al., 1990]. The formation of (Al) , $\text{Al}_{13}\text{Fe}_4$, $\text{Al}_6\text{Mn}(\text{Cu}, \text{Fe})$, $\text{Al}_7\text{Cu}_2\text{Fe}$ and Al_2Cu was reproduced in the Scheil simulation. Al_3Ti appeared as the primary phase due to the Ti addition.

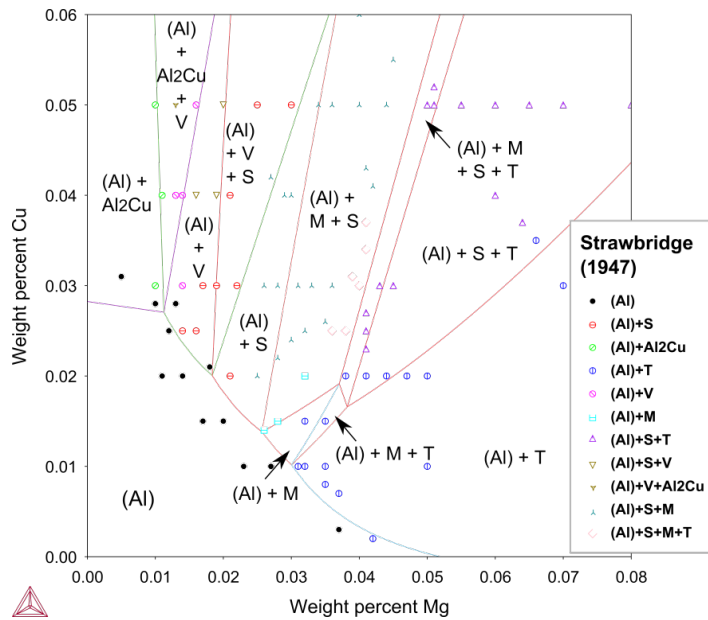


Figure 19: Calculated isothermal sections of the Al-Cu-Mg-Zn system at 460°C: at 8 wt. % Zn [Chen, 2012b] (experimental data are from Strawbridge et al. [1947]).

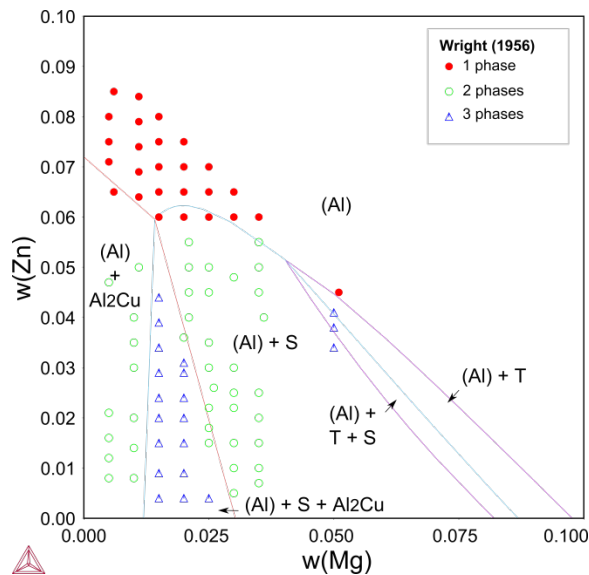


Figure 20: Calculated isothermal sections of the Al-Cu-Mg-Zn system at 90 wt.% Al (experimental data are from Wright [1956]).

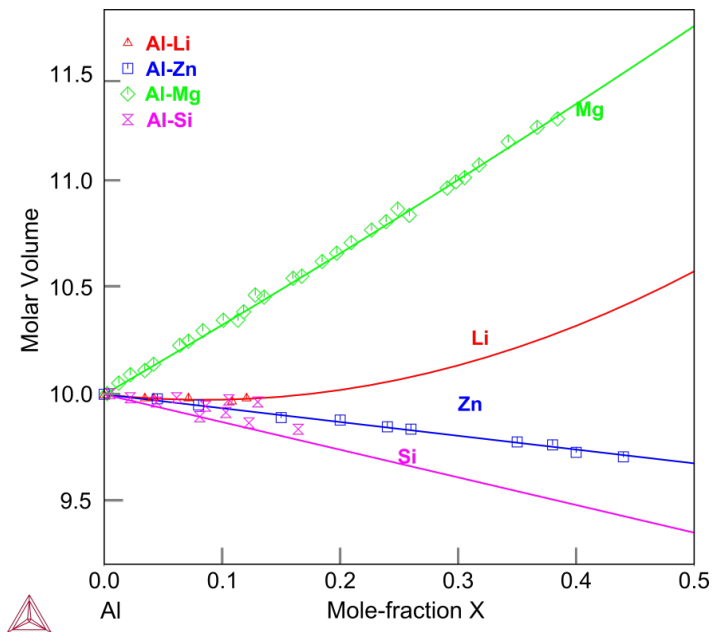


Figure 21: Calculated molar volumes of the Al-X (X=Li, Mg, Si, Zn) fcc_A1 phase.

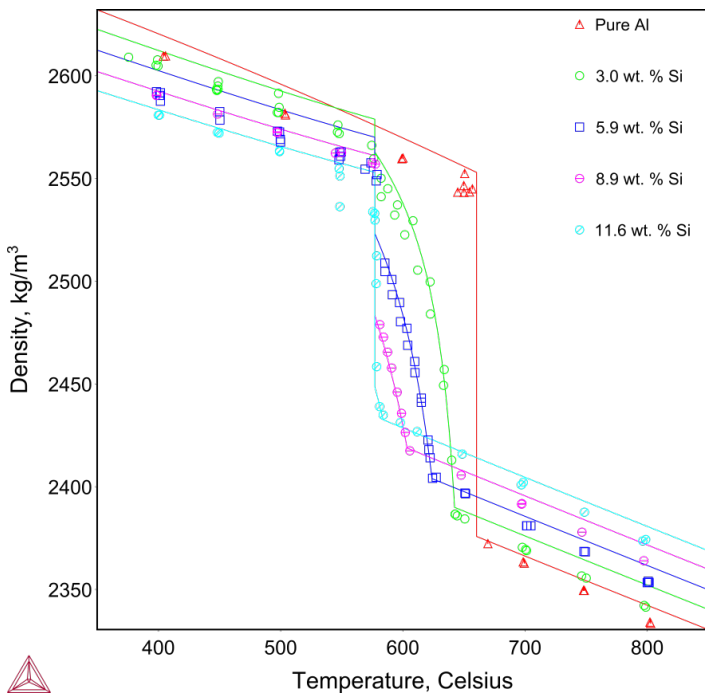


Figure 22: Calculated densities of pure Al and Al-Si alloys versus the temperature, in comparison with experimental data from Magnusson and Arnberg [2001].

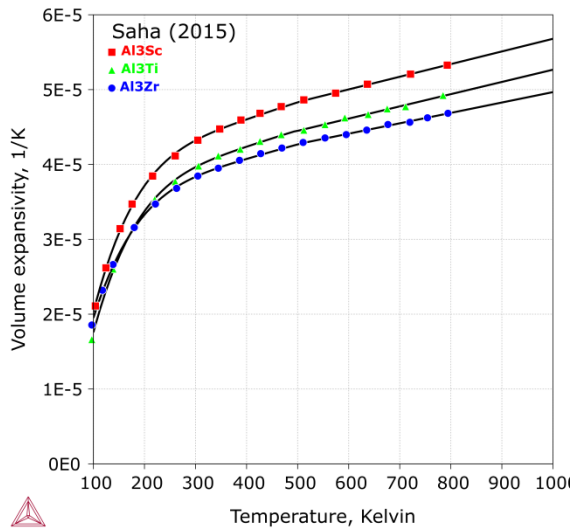


Figure 23: Calculated volume thermal expansivity for Al_3Sc , Al_3Ti and Al_3Zr [Chen, 2017e].

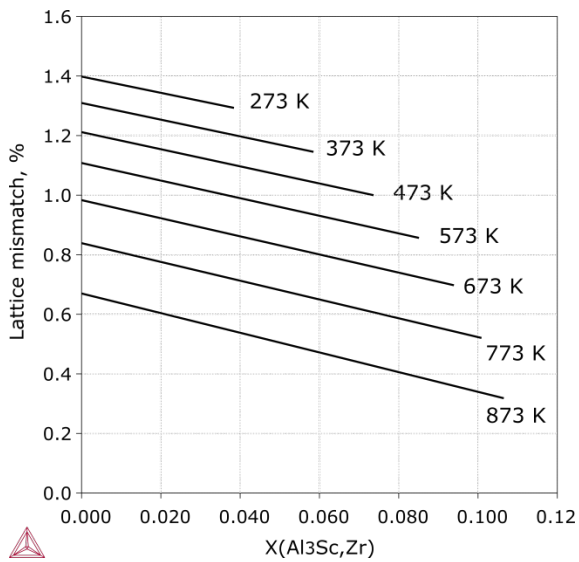


Figure 24: Lattice mismatch between Al_3Sc and (Al), at different Zr contents and temperatures [Chen, 2017e].

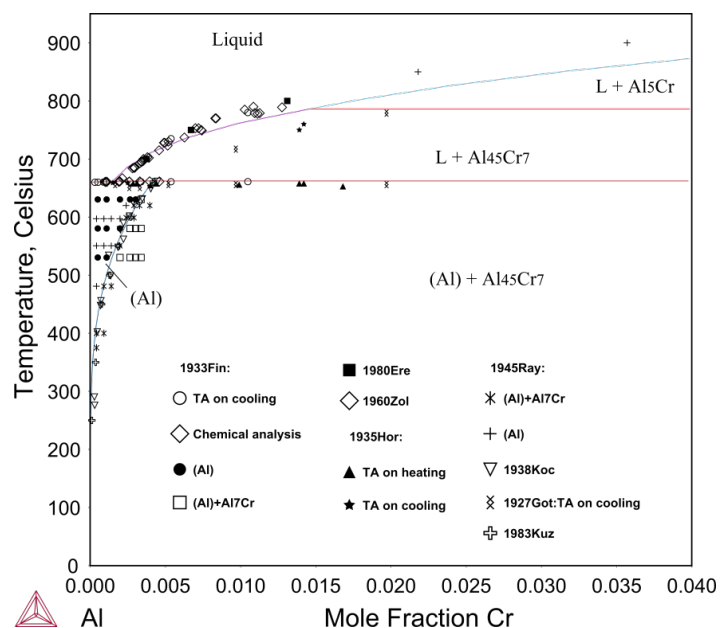


Figure 25: Calculated Al-rich Al-Cr binary phase diagram. Experimental data are from Fink and Freche [1933], Raynor and Little [1945] and Eremenko et al. [1980].

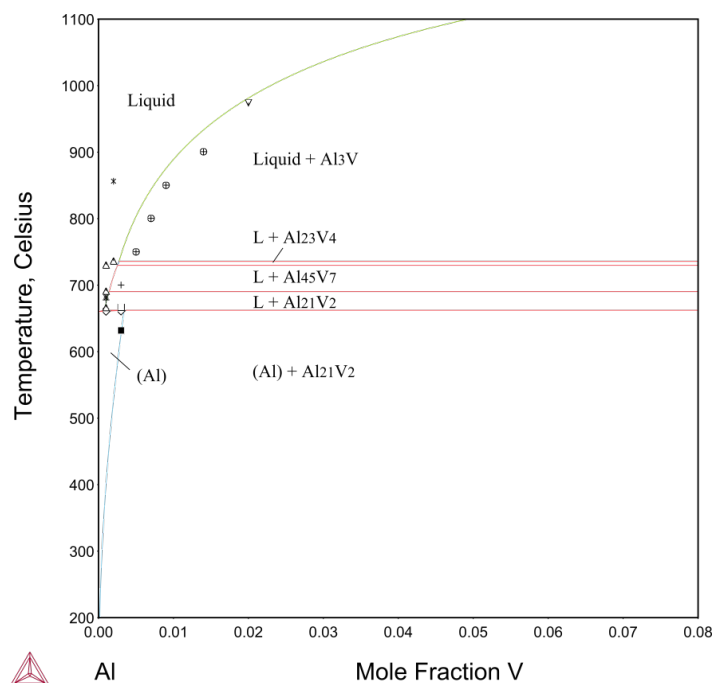


Figure 26: Calculated Al-rich Al-V binary phase diagram. Experimental data were read from Gong et al. [2004].

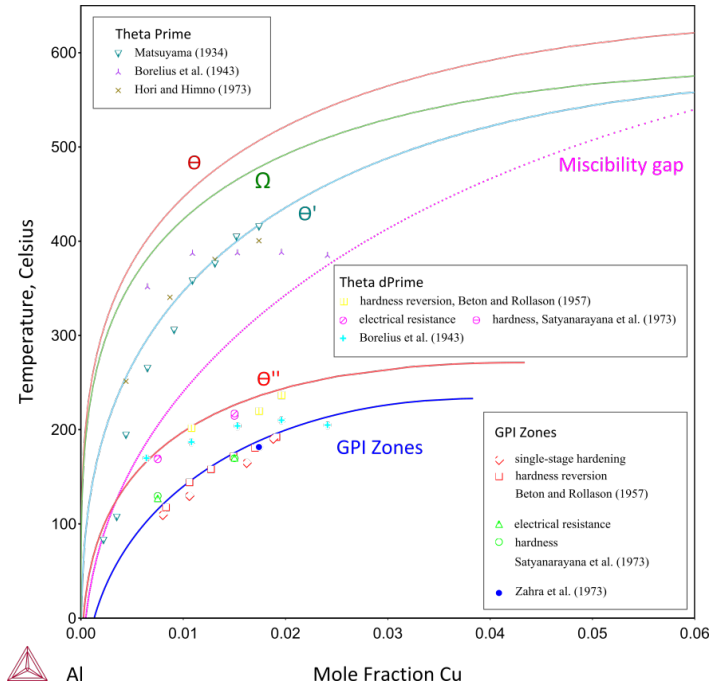


Figure 27: Calculated Al-Cu (Al) solvus curves equilibrated with θ , Ω , θ' , θ'' (or GPII zones) and GPI zones, respectively. A metastable miscibility gap of fcc_A1 is shown. The GPI zones were modeled as the second composition set of fcc_A1, i.e. fcc_A1#2. It is assumed that experimentally observed GPI zones are usually tiny (say < 3 nm), so the interfacial and elastic energy are considered. The line for GPI zones was calculated with adding +800 J/mole-atoms to the energy of fcc_A1#2 [Chen, 2014b].

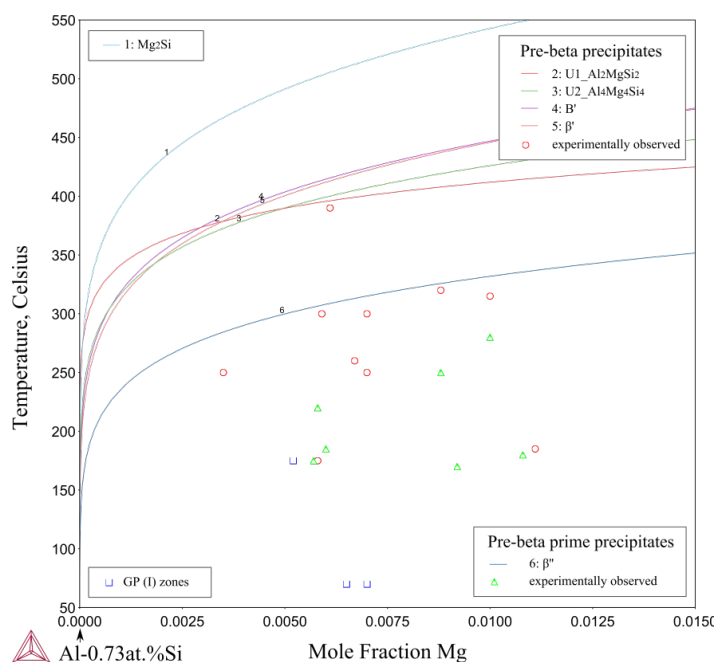


Figure 28: Calculated fcc_Al solvi in alloys at 0.73 at.% Si and varying Mg content, relative to different Al-Mg-Si precipitates, including the stable β -Mg₂Si phase, pre- β precipitates (β' , U1, U2 and B') and the pre- β' precipitate, i.e. β'' . The symbols indicate certain precipitates have been experimentally observed in alloys of given compositions and aged at given temperatures [Chen, 2014b].

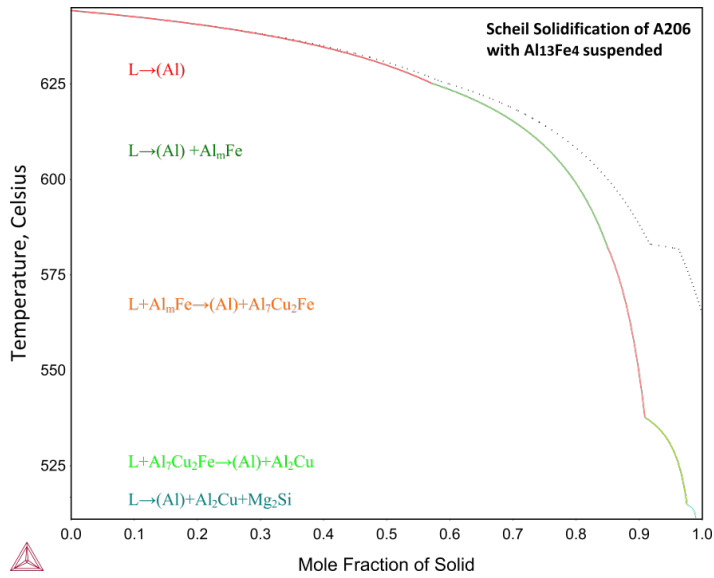


Figure 29: Scheil solidification of an A206 alloy (Al-4.58Cu-0.28Mg-0.51Fe-0.07Si-0.003Mn, wt.%) with the $Al_{13}Fe_4$ phase suspended [Chen, 2014b]. According Liu et al. [2012], the metastable Al_mFe phase formed after (Al) during the solidification. The phase formation sequence and phase transformation temperatures can be well accounted for with this calculation.

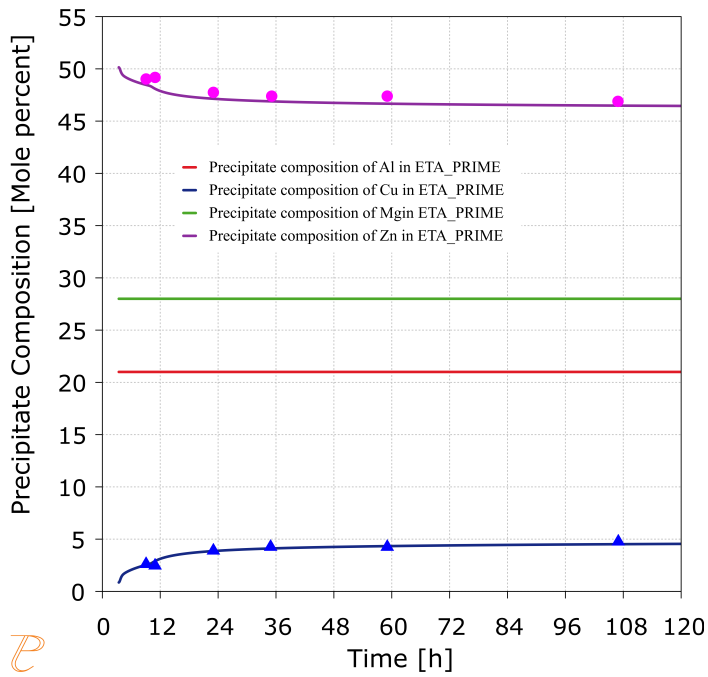


Figure 30: Solutes in the eta_prime precipitates that form during the aging treatments (from 20 °C to 120 °C at 30 °C/h, 120 30 °C for 6 h, from 120 °C to 135 °C at 15 °C/h, and 135 °C) of a PA alloy of the 7xxx series. Curves are from the Precipitation Module (TC-PRISMA) simulations. Experimental data are from [2010, Marlaud].

TCAL6 References

- [1933, Fink] W. L. Fink, H. R. Freche, Equilibrium relations in aluminum–chromium alloys of high purity. Trans. Am. Soc. Met. AIME. 104, 325–334 (1933).
- [1940, Takeda] S. Takeda, K. Mutuzaki, The equilibrium diagram of the Fe–Al–Si system. Tetsu-to-Hagane. 26, 335–361 (1940).
- [1945, Raynor] G. V. Raynor, K. Little, The constitution of the aluminium-rich alloys of aluminium, chromium, and manganese. J. Inst. Met. 71, 493–524 (1945).
- [1948, Strawbridge] D. J. Strawbridge, A. Little, The Constitution of Aluminium Copper Magnesium Zinc Alloys At 460 °C. J. Inst. Met. 74, 191–225 (1948).
- [1956, Wright] E. H. Wright, “Equilibrium relations at 460 °C in aluminum-copper-magnesium-zinc alloys of high purity” (Internal Report 13–56-EC2, Aluminum Research Laboratories, Aluminum Company of America, 1956).
- [1967, Munson] D. Munson, A Clarification of the Phases Occurring in Aluminium-Rich Aluminium-Iron-Silicon Alloys, with Particular Reference to the Ternary Phase α -AlFeSi. J. Inst. Met. 95, 217–219 (1967).
- [1980, Eremenko] V. N. Eremenko, Y. V. Natanzon, V. P. Titov, Kinetics of chromium dissolution in aluminum at 700–900 °C. Izv. Akad. Nauk SSSR. Metall. 6, 217–220 (1980).
- [1986, Fujikawa] S. Fujikawa, Solvuses of delta’ phase (Al₃Li) and delta phase (AlLi) in Al-Li alloys. J. Japan Inst. Light Met. 36, 771–777 (1986).
- [1988, Zakharov] A. M. Zakharov, I. T. Gulman, A. A. Arnold, Y. A. Matsenko, Phase diagram of the Aluminium-Silicon-Iron system in the concentration range of 10–14% Si and 0–3% Fe. Russ. Metall. 3, 177–180 (1988).
- [1989, Saunders] N. Saunders, Calculated stable and metastable phase equilibria in Al-Li-Zr alloys. Zeitschrift fur Met. 80, 894–903 (1989).
- [1990, Backerud] L. Backerud, G. Chai, J. Tamminen, Solidification Characteristics of Aluminum Alloys in Foundry Alloys, Volume 1 and 2 (American Foundrymen’s Society, Inc., 1990), p. 266.
- [1993, an Mey] S. an Mey, Reevaluation of the Al-Zn system. Zeitschrift fur Met. 84, 451–455 (1993).
- [1993, Schmid-Fetzer] R. Schmid-Fetzer, Aluminium-Silicon-Tin, in Ternary Alloys Volume 8 (VCH, 1993), pp. 263–269.
- [1997, Ansara] I. Ansara, N. Dupin, H. L. Lukas, B. Sundman, Thermodynamic assessment of the Al-Ni system. J. Alloys Compd. 247, 20–30 (1997).

- [1998, Liang] P. Liang et al., Experimental investigation and thermodynamic calculation of the Al–Mg–Zn system. *Thermochim. Acta.* 314, 87–110 (1998).
Updated by H.-L. Chen in 2012 during the database construction.
- [2001, Magnusson] T. Magnusson, L. Arnberg, Density and solidification shrinkage of hypoeutectic aluminum-silicon alloys. *Metall. Mater. Trans. A.* 32, 2605–2613 (2001).
- [2004, Bosselet] F. Bosselet, S. Pontevichi, M. Sacerdote-Peronnet, J. C. Viala, Experimental measurement of the Al-Fe-Si isothermal section at 1000 K. *J. Phys. IV.* 122, 41–46 (2004).
- [2004, Gong] W. Gong et al., Thermodynamic reassessment of the Al–V system. *Zeitschrift fur Met.* 95, 978–986 (2004).
- [2004, Pontevichi] S. Pontevichi, F. Bosselet, F. Barbeau, M. Peronnet, J. C. Viala, Solid-liquid phase equilibria in the Al-Fe-Si system at 727 °C. *J. Phase Equilibria Diffus.* 25, 528–537 (2004).
- [2007, Du] Y. Du et al., Reassessment of the Al–Mn system and a thermodynamic description of the Al–Mg–Mn system. *Int. J. Mater. Res.* 98, 855–871 (2007).
- [2009, Sun] W.-H. Sun et al., Experimental investigation and thermodynamic modeling of the Cu–Mn–Ni system. *Calphad.* 33, 642–649 (2009).
- [2010, Marlaud] T. Marlaud, A. Deschamps, F. Bley, W. Lefebvre, B. Baroux, "Influence of alloy composition and heat treatment on precipitate composition in Al-Zn-Mg-Cu alloys", *Acta Mater.* 58 (2010) 248-260.
- [2012, Chen] H.-L. Chen, "Modeling of the $AlLi_2$ and Al_3Li phases in the Al-Li binary system", unpublished work, 2012a/2017b.
- [2012, Guo] C. Guo, C. Li, P.J. Masset, Z. Du, A thermodynamic description of the Al-Mo-Si system, *Calphad* 36 (2012)100-109.
- [2012, Liu] K. Liu, X. Cao, X. G. Chen, A New Iron-Rich Intermetallic-Al m Fe Phase in Al-4.6Cu-0.5Fe Cast Alloy. *Metall. Mater. Trans. A.* 43, 1097–1101 (2012).
- [2012b, Chen] H.-L. Chen, "Thermodynamic assessment of the Al-Cu-Mg-Zn(-Fe) and Al-Cu-Mg-Si multicomponent alloy systems" (Stockholm, Sweden, 2012), unpublished work.
- [2014a, Chen] H. Chen, Q. Chen, Y. Du, J. Bratberg, A. Engström, Update of Al-Fe-Si, Al-Mn-Si and Al-Fe-Mn-Si thermodynamic descriptions - TNMSC. *Chinese J. Nonferrous Met.* 24, 2041–2053 (2014).
- [2014b, Chen] H.-L. Chen, "Thermodynamic modeling of metastable precipitate phases in Al-Cu, Al-Fe, Al-Mg-Si, and Al-Mg-Zn based alloys" (Stockholm, Sweden, 2014), unpublished work.
- [2017a, Chen] H.-L. Chen, "Thermodynamic modeling of the Er-X (X = Ag, Al, Fe, Si, Zr) binary and Al-Er-X (X=Cu, Fe, Mg) ternary systems" (Stockholm, Sweden, 2017), unpublished work.
- [2017c, Chen] H.-L. Chen, "Thermodynamic modeling of the Al-Sn-X (X = Cd, Cu, In, Si, Zn) ternary systems" (Stockholm, Sweden, 2017), unpublished work.

[2017d, Chen] H.-L. Chen, "Thermodynamic modeling of the Al-Ce-X (X = Cr, Fe, Mg, Mn, Ni, Si) ternary systems" (Stockholm, Sweden, 2017), unpublished work.

[2017e, Chen] H.-L. Chen, "Thermodynamic modeling of phase equilibria and molar volume in the Sc-Ti, Al-Sc-Si, Al-Sc-Ti, Al-Sc-Zr and Al-Si-Ti systems" (Stockholm, Sweden, 2017), unpublished work.

Scientific Bibliography

See the Thermo-Calc Software scientific bibliography at: <https://www.thermocalc.com/support/resources/>.

TCAL6 Included Phases

The elements in phase names are rearranged in the alphabetical order except for carbides and borides, where B and C appear at the end. In order to designate the high-temperature and the low-temperature modifications of a phase, respectively, suffixes of “_HT” and “_LT” are used instead of using prefixes of “alpha-”, “beta-” or “gamma”.

LIQUID
FCC_A1
FCC_L12
BCC_A2
BCC_B2
CBCC_A12
CUB_A13
DHCP
HCP_A3
BETA_RHOMBO_B
GRAPHITE
RHOMBO_A7
TETRA_A6
C14_LAVES
C15_LAVES
C36_LAVES
DIAMOND_A4
BCT_A5
ORTHORHOMBIC_GA

SIGMA
AL45V7
CUZR2_C11B
B2_BCC
ALB2_C32
FEB_B27
AL3TI_D022
ALZR2_B82
CAZN13_CF112
NI3SN_D019
CRB_B33
AL3ZR5_D8M
AL2SR_OI12
CACU5_D2D
M3B4_D7B
SI2ZR3_D5A
CO2SI_C23
CR5B3_D81
M11GE8_OP76
SIZR3_TP32
SI4ZR5_TP36
SI2ZR_C49
SI2TI_C54

ZRM5_C15B
FEM_B35
SN5Ti6_OI44
M7C3_D101
M23C6_D84
V_PHASE
AGER
AG2ER
AG51ER14
AGLA
AG2LA
AG51LA14
AG5LA
AGMG3
AGMG4
AG2NA
AGZN3
AGZN
AG5ZN8
ALCU_DEL
ALCU_EPS
ALCU_ETA
AL2CU_C16
AL2CU_OMEGA

THETA_PRIME
THETA_DPRIME
ALCU_ZETA
GAMMA_D83
GAMMA_H
ALER
AL2ER3
ALER2
AL2FE1
AL5FE2
AL5FE4
AL13FE4
AL4FE
ALMG_BETA
ALMG_EPS
ALMG_GAMMA
ALMGZN_PHI
AL12MN
AL6MN
AL4MN_R
AL4MN_U
AL11MN4_LT
AL11MN4_HT

AL8MN5
AL12MO
AL5MO
AL22MO5
AL17MO4
AL4MO
AL3MO
AL8MO3
AL63MO37
ALMO3
AL3NI_D011
AL3NI2
AL3NI5
CA2CU
CACU
HCP_CA
CAH2_LT
CAH2_HT
CALI2
CA2NI7
CANI3
CA3SI4
CA14SI19
CASI2

CA3ZN
CA5ZN3
CAZN
CAZN2
CAZN3
CAZN11
CU9ER2
CU7ER2
CU5ER_C15B
CU2ER
CUER_B2
CU9GA4_0
CU9GA4_1
CU9GA4_2
CU9GA4_3
CUGA2
CUGA_THETA
CU5HF
CU51HF14
CU8HF3
CU10HF7
CU1HF2
CUIN_GAMMA

CUIN_THETE
CU2IN_HT
CU2IN_LT
CU11IN9
CU37LA3
CU6LA1_LT
CU6LA1_HT
CU5LA1
CU4LA1
CU2LA1
CU1LA1
CUMG2
CU4SC
CU2SC_C11B
CUSC
CU33SI7_DELTA
CU15SI4_EPSILON
CU56SI11_GAMMA
CUSI_ETA
EPSILON
FE3ER
FE23ER6
FE17ER2
MG24R5

ER5SI3
ER5SI4
ERSI_OC8
ERSI_OP8
ERSI2
C14_FE2HF
C36_FE2HF
C15_FE2HF
FE1HF2
FE2SC_C15
FE6SC29
FE2SI
FESI2_H
FESI2_L
FESI_B20
MN5SI3_D88
GAMMA_D82
FEZN_GAMMA1
FEZN_DELTA
FEZN_ZETA
LAH3
MGH2
HFMN

KNA2
KZN13
LA3NI
LA7NI3
LANI
LA2NI3
LA7NI16
LANI3
LA2NI7_LT
LA2NI7_HT
LANI5
LA3SI2
LA5SI3
LA5SI4
LASI
LASI2_A1
LASI2_A2
LAZN2
LAZN4
LAZN5
LA3ZN22
LAZN11
LAZN13
LA2ZN17

LI2ZN3_L
LI2ZN3_H
LI2ZN5_L
LI2ZN5_H
LIZN4_L
LIZN4_H
LIZN2
BCC_B32
MG2NI
MG2SI_C1
MG7ZN3
MGZN
MG2ZN3
L10_TETRA
MNNI2
MNSC4
MN11SI19
MN3SI
MN6SI
MN9SI2
MNZN9
NASI_LT
NASI_HT

NAZN13
NI5HF
NI7HF2
NI3HF_LT
NI3HF_HT
NI21HF8
NI7HF3
NI10HF7
NI11HF9
NIHF_LT
NIHF_HT
NIHF2
HF2SI
HF3SI2
HF5SI3
HFSI
HF5SI4
HFSI2
TET_A6P
NI2SI_HT
NI3SI2
NI3SI_HT
L12_FCC
NI3SI_MT

NI5SI2
NISI_B31
NISI2
NIZN_LT
NIZN8
ALB12
AL4C3
AL5CR
AL4CR
ALCR_GAMMA1
GAMMA_D810
AL7SR8
AL4M_D13
AL2TI
AL5TI2
AL5TI3
AL3TI_LT
ALTI3_D019
AL21V2
AL23V4
AL8V5
AL4ZR5
AL3ZR2_OF40

AL2ZR3_TP20
AL3ZR_D023
CU6SN5_HT
CUSN_GAMMA
CU10SN3
CU3SN
CU41SN11
CU6SN5_LT
CUSR
CU2TI
CU3TI2
CU4TI1
CU4TI3
CUTI_B11
CUTI3
CU10ZR7
CU51ZR14
CU8ZR3
FE2GE1
FEGE_ETA
FE6GE5
FE2GE3
FE5SN3_D82
FE3SN2

FEZR3
MGB4
MGB7
MG2C3
MGC2
MG2SR
MG38SR9
MG23SR6
MG17SR2
MN2B_D1F
MNB4
M5C2
CR3MN5
HIGH_SIGMA
GEMN3_HT
GE2MN3
GE2MN5
GE3MN7
MN2SN
MN3SN2
MNTI_LT
MNTI_HT
MN3TI

MN4TI
MNV_SIGMA
NI4B3_ORTH
NI4B3_MONO
GENI2
GE3NI5_HT
GE2NI3
GENI3_GAMMA
GE2NI5
GE3NI5_LT
GE12NI19
NI7SC2
NISC_B2
NISC2
NI3SN2_LT
NI3SN_HT
NI3SN2_HT
NI3SN4
NISR
NI3TI_D024
NIT12
NI2V7
NI2V1
NI10ZR7

NI21ZR8
NI11ZR9
NI7ZR2
SC5SI3
SCSI
SC3SI5_LT
SC3SI5_HT
SCZN
SCZN2
SC13ZN58
SC3ZN17
SCZN12
SIB3
SIB6
SIBX
SIC
CR3SI
CRSI2_C40
SI2SR_HT
SI2SR_LT
SI3TI5_D88
V3SI
CRZN13

CRZN17
SRZN5_LT
TIZN2
TIZN5
TIZN10
TIZN15
V4ZN5
ZN2ZR
ZN22ZR
ZN39ZR5
ZN3ZR_LT
ZN3ZR_HT
B4C
CR2B_ORTH
CRB4
SRB6
V2B3
V5B6
ZRB12
CU6CE
CU5CE
CU4CE
CU2CE
CUCE

CE2FE17
MGCE
MG3CE
MG41CE5
MG17CE2
MG12CE
CE5SI3
CE3SI2
CE5SI4
CESI
CE3SI4
CE3SI5
CESI2
CE7NI3
CENI
CENI2
CENI3
CE2NI7
CENI5
CR3C2
V3C2
CDCU2
CD3CU4

CD8CU5
CD10CU3
SN_HP1
CR3GE
CR5GE3_HT
CR5GE3_LT
CR11GE19
GE2SR
GE3TI5
V3GE
V17GE31
SR3SN5
SRSN3
SRSN4
SN3TI2
V3SN
VSN2
SN3ZR5
SNZR3_A15
V2ZR
AL14CA13
AL3CA8
AL4CE
AL11CE3

AL3CE_H
AL3CE_L
ALCE
ALCE2
ALCE3_H
ALCE3_L
AL13CO4
AL3CO
AL5CO2
AL9CO2
AL3LA
ALLA
AL53LA22
AL11LA3_LT
AL11LA3_HT
AL2LI3
ALLI2
AL4LI9
B32_ALLI
AL3X
AL2SC
ALSC
AL3HF4

LI22SI5
LI13SI4
LI7SI3
LI12SI7
AG9CA2
AG7CA2
AG2CA
AGCA3
AG4SC
AGSC
AL4C4SI
AL8C7SI
AL20CECR2
AL8CEM4
AL10CE2M7
AL3CECU
ALCEM
ALCE2CU2
ALCEFE
AL10CEFE2
AL8CEFE2
AL13CEMG6
AL2CENI
AL5CE2NI5

AL4CENI
AL5CE1NI2
AL23CE4NI6
AL60CE12NI28
AL40CE30NI30
ALCESI
AL7CE5SI3
ALCESI2
AL4CE3SI6
AL13CR4SI4
AL9CR3SI
ALCRSI_T3
ALCRSI_T4
AL9CU6ER5
AL5CU3ER2
AL3CU1ER1
AL62CU25FE13
AL7CU2FE
AL10CU10FE
AL2CULI
ALCULI_T2
ALCULI_R
ALCULI_B

Q_PHASE
S_PHASE
S_PRIME
T_PHASE
AL28CU4MN7
AL11CU5MN3
ALCU3MN2
AL7CU4NI
ALCUSC_TAU
AL6ER2FE11
AL7ERMG2
AL9FENI
AL10FE3NI
AL71FE5NI24
ALFESI_T1
ALFESI_T2
ALFESI_T3
ALFESI_T4
AL8FE2SI
AL9FE2SI2
ALFESI_T7
ALFESI_T8
ALFESI_T10
ALFESI_T11

ALFEZN_GAMMA
ALLIMG_T
ALLISI
AL3LI8SI5
ALLI5SI2
ALLI2ZR
AL18MG3MN2
ALMG3NI2
BETA_PRIME
B_PRIME
U1_AL2MGSI2
U2_AL4MG4SI4
BETA_DPRIME
ETA_PRIME
T_PRIME
AL31MN6NI2
AL2MN2SI3
AL5MN6SI7
AL1MN1SI1
AL3MNSI2
AL3MN4SI2
ALMNSI_T6
ALMNSI_T8

AL15SI2M4
AL2MNSI3
AL24MN5ZN
AL9MN2ZN
AL11MN3ZN2
ALNI2SI
AL6NI3SI
ALNI16SI9
ALNI2ZN
AL13NI38ZN49
ALSC2SI2
ALSI3TI2
ALSI7TI4
CULIMG_T
CU16MG6SI7
CU3MG2SI
CU5MN4SI
CUMNZN
CU6NISI3
CU46NI25SI29
FE5NI3SI2
ZN13M2
MG6MN3NI
MGNI6SI6

MG2NI3SI
MG10NI55SI35
MG2NI16SI11
MG5NI9SI
MG9NI29SI16
MGNI6ZN6
MN15NI45SI40
MN15NI50SI35
MN6NI16SI7
MN1NI1SI1
MNNISI_T5
MNNISI_T6
MN3NI2SI
MN2NISI
MN6NISI3
MN66NI4SI30
MN52NI29SI19
MN7NI7ZN86
NI2SIZN_T1
NI9SI2ZN_T2
NI2SIZN3_T3
NISIZN_T4
Q_ALCUMGSI
AL18FE2MG7SI10

TCAL6 Models for the Included Phases

LIQUID			
:AL CU ER FE MG MN MO NI SI ZN B C CR GE SN SR TI V ZR MG2GE MG2SN1 ZN2ZR AG CA HF H LIH K LA LI NA SC CO PB BE BI CE CD GA IN :			
> Metallic LIQUID solution phase			
FCC_A1	2	1	1
:AL CU ER FE MG MN MO NI SI ZN CR GE SN SR TI V ZR AG CA HF K LA LI NA SC CO PB BE BI CE CD GA IN:B C H VA :			
> Metallic FCC_A1 solution, e.g. (Al), (Cu), and MC carbides			
ORD_L12	3	0.75	0.25 1
:AL CU ER FE MG MN MO NI SI ZN CR GE SN SR TI V ZR AG CA HF K LA LI NA SC CO PB BE BI CE CD GA IN:AL CU ER FE MG MN MO NI SI ZN CR GE SN SR TI V ZR AG CA HF K LA LI NA SC CO PB BE BI CE CD GA IN:B C H VA :			
> Solution of ordered FCC_L12, having Gibbs energy contribution from DISO_A1			
DISO_A1	2	1	1
:AG AL% BE BI CA CD CE CO CR CU ER FE GA GE HF IN K LA LI MG MN MO NA NI PB SC SI SN SR TI V ZN ZR : VA :			
> Disordered part of the ORD_L12 phase. NOT an independent phase!			
BCC_A2	2	1	3
:AL CU ER FE MG MN NI SI ZN VA GE CR SN SR TI V ZR AG CA HF K LA LI NA SC CO PB BE BI CE CD GA IN:B C H VA :			
> Metallic BCC_A2 solution			
BCC_B2	3	0.5	0.5 3
:AL CU ER FE MG MN MO NI SI TI ZN VA GE CR SN SR V ZR AG CA HF K LA LI NA SC CO PB BE BI CE CD GA IN:AL CU ER FE MG MN MO NI SI TI ZN VA GE CR SN SR V ZR AG CA HF K LA LI NA SC CO PB BE BI CE CD GA IN:B C H VA :			
> Solution of ordered BCC_B2, having Gibbs energy contribution from BCC_A2			
CBCC_A12	2	1	1

:AL CO CU FE LI MG MN NI SI ZN CR GE SN SR TI V ZR:B C H VA :		
CUB_A13	2	1 1
:AL CE CU FE HF LI MG MN NI SI ZN CR GE SN SR TI V ZR AG:B C H VA :		
DHCP		
:CU LA NI SC :		
HCP_A3	2	1 0.5
:AG AL CU ER FE K LI MG MN MO NA NI SI ZN GE CR SN SR TI V ZR HF LA SC CO PB BE BI CA CE CD GA IN:B C H VA :		
> Metallic HCP_A3 solution, alpha_Mg/Hf/Sc/Ti/Zr, epsilon_CuZn, etc.		
BETA_RHOMBO_B	2	93 12
:B:CU SI B C :		
GRAPHITE		
:B C :		
RHOMBO_A7		
:BI IN SN :		
TETRA_A6		
:IN SN :		
C14_LAVES	2	2 1
:AL CU CR FE HF LI MG MN NI TI ZN ZR:AL CU CR ER FE HF MG MN SC TI ZN ZR :		
> Solution of MgZn ₂ -type phases, including MgZn ₂ (Eta, aka M or sigma)		
C15_LAVES	2	2 1
:AL CA CU FE LI MG NI SC SI ZN CR TI ZR LA HF:AL CA CE CU ER FE LI MG NI SC SI ZN CR TI ZR LA HF :		
> Solution of Cu ₂ Mg-type phases, cF24, Fd-3m		
C36_LAVES	2	2 1
:AL CU CR FE HF MG MN NI ZN ZR:AL CU CR FE HF MG NI SC ZN ZR :		
> Solution of MgNi ₂ -type phases, hP24, P63/mmc		

DIAMOND_A4		
:AL SI ZN B C GA GE SR SN TI :		
> Pure C, Ge, Si or solution phases based on them		
BCT_A5		
:AL B BI CD CU GA GE IN ZN PB SN TI :		
> Pure Sn or its solution		
GAS		
:AL AL2 B B2 C C2 C3 C4 C5 C60 CA CA2 CO CO2 CR CR2 CU CU2 FE FE2 GE GE2 LI LI2 MG MG2 MN NI NI2 SC SI SI2 SI3 SN SN2 SR SR2 TI TI2 V ZN K K2 NA NA2 H H2 AL1H1 AL1H2 AL1H3 CA1H1 CU1H1 H1LI1 H1NA1 K1LI1 :		
ORTHORHOMBIC_GA		
:GA :		
SIGMA	3	8 4 18
:FE MN NI:CR V:FE CR MN NI V :		
AL45V7	2	45 7
:AL:CR V :		
> Al45Cr7, Al45V7		
CUZR2_C11B	2	1 2
:AL CR CU SI ZN:AL CR TI ZR :		
> AlCr2, CuTi2, CuZr2, Ti2Zn, ZnZr2		
B2_BCC	2	1 1
:AL CO FE CU ZN:CO MN TI VA ZR :		
> CuZr, FeTi, TiZn, ZnZr, MnZn(rt), AlCo		
ALB2_C32	2	1 2
:MG AL MN CR ZR TI V:B :		
> AlB2, B2Cr, B2Mg, B2Mn, B2Ti, B2V, B2Zr		

FEB_B27	2 1 1
:FE MN TI ZR SR: B SI ZN GE :	
> BFe, BMn, BTi, GeZr, SiTi, SrZn, SiZr	
AL3TI_D022	2 3 1
:AL MN NI SI TI:AL GE MN SC TI V ZR :	
> Al3Ti, Ni3V, GeMn3, Al3V	
ALZR2_B82	2 1 2
:AL GE MN SN VA:ZR MN SC TI VA :	
> SnTi2, GeMn2, AlZr2, AlSc2	
CAZN13_CF112	2 1 13
:CA SR:ZN :	
> CaZn13, SrZn13	
NI3SN_D019	2 1 3
:AL SN GE VA:LA MN FE NI TI :	
> Ni3Sn, SnTi3, SnMn3, AlLa3	
CRB_B33	2 1 1
:AL CA CR NI SR V:AG B SI GE SC SN ZR HF :	
> AgCa, AlHf, AlZr, BNi, BV, GeSr, NiZr, SiSr, SnSr	
AL3ZR5_D8M	2 3 5
:AL SI GE:ZR CR V :	
> Al3Zr5, Cr3Si5, Ge3V5, Si3V5	
AL2SR_OI12	2 2 1
:AL ZN:SR :	
> Al2Sr, SrZn2	
CACU5_D2D	2 1 5

:CA SC SR:CU NI ZN :		
> CaCu ₅ , CaNi ₅ , CaZn ₅ , Cu ₅ Sr, ScNi ₅ , SrZn ₅		
M3B4_D7B	2	4 3
:B:MN CR TI V :		
> V ₃ B ₄ , Ti ₃ B ₄ , Mn ₃ B ₄ , Cr ₃ B ₄		
SI2ZR3_D5A	2	2 3
:SI B:ZR V :		
> Si ₂ Zr ₃ , B ₂ V ₃		
CO2SI_C23	2	2 1
:CA CU FE NI SR:AL SI ZN GE SN :		
> Ca ₂ Si, Ni ₂ Si, SiSr ₂ , SnSr ₂ , GeSr ₂		
CR5B3_D81	2	0.625 0.375
:CA CR SR:AG SI B GE SN :		
> Ca ₅ Si ₃ , Sn ₃ Sr ₅ , Si ₄ Sr ₅ , Ge ₃ Sr ₅ , B ₃ Cr ₅		
M11GE8_OP76	2	0.579 0.421
:CR V:GE :		
> Cr ₁₁ Ge ₈ , V ₁₁ Ge ₈		
SIZR3_TP32	2	1 3
:SI GE:ZR TI :		
> SiZr ₃ , SiTi ₃ , GeZr ₃		
SI4ZR5_TP36	2	4 5
: SI GE:TI ZR :		
> Si ₄ Zr ₅ , Si ₄ Ti ₅ , Ge ₄ Zr ₅		
SI2ZR_C49	2	2 1
:SI GE:ZR :		

> Si2Zr, Ge2Zr		
SI2TI_C54	2	2 1
:AL GE SI SN:TI ZR :		
> Ge2Ti, Si2Ti, Sn2Zr		
ZRM5_C15B	2	5 1
:CU NI:ZR :		
> Cu5Zr, Ni5Zr		
FEM_B35	2	1 1
:FE:SN GE :		
> FeSn, FeGe		
SN5TI6_OI44	2	5 6
:GE SN SI:V TI :		
> Sn5Ti6, Si5V6, Ge5Ti6		
M7C3_D101	2	7 3
:MN CR:C :		
> Cr7C3, Mn7C3		
M23C6_D84	2	23 6
:MN CR:C SC :		
> Cr23C6, Mn23C6, Mn23SC6		
V_PHASE	3	5 6 2
:AL SI ZN:CU ZN:Mg :		
> solution of Mg2Zn11, Al5Cu6Mg2; aka Z		
AGER	2	1 1
:AG:ER :		
AG2ER	2	2 1

:AG:ER :				
AG51ER14	2	0.77	0.23	
:AG:ER :				
AGLA	2	1	1	
:LA:AG :				
AG2LA	2	1	2	
:LA:AG :				
AG51LA14	2	14	51	
:LA:AG :				
AG5LA	2	1	5	
:LA:AG :				
AGMG3	2	0.23	0.77	
:AG:MG :				
> Ag17Mg54				
AGMG4	2	0.2	0.8	
:AG:MG :				
> Ag9Mg37				
AG2NA	2	2	1	
:AG:NA :				
AGZN3				
:AG ZN :				
AGZN	2	1	2	
:ZN:AG ZN :				
AG5ZN8	4	2	2	3
:AG ZN:AG:AG ZN:AG ZN :				

ALCU_DEL	2 2 3	:AL ZN:CU FE :
ALCU_EPS	2 1 1	:AL CU ZN NI:CU FE :
ALCU_ETA	2 1 1	:AL CU:CU FE ZN NI :
AL2CU_C16	2 2 1	:AL FE GE SN ZR MN NI HF:AL CU FE NI B MN SI : > Al ₂ Cu, AlHf ₂ , Fe ₂ B, FeGe ₂ , FeZr ₂ , FeSn ₂ , Mn ₂ B, MnSn ₂ , NiB ₂ , NiZr ₂ , SiZr ₂
AL2CU_OMEGA	2 2 1	:AL:CU : > Al ₂ Cu-OMEGA metastable precipitate
THETA_PRIME	2 2 1	:AL:CU :
THETA_DPRIME	2 3 1	:AL:CU :
ALCU_ZETA	2 9 11	:AL:CU FE :
GAMMA_D83	3 4 1 8	:AL FE NI SI ZN:AL CU NI SI ZN:AG CU MN FE NI ZN : > solution between Al ₈ Cu ₅ (rt) and Cu ₅ Zn ₈
GAMMA_H	3 4 1 8	:AL ZN:AL CU ZN:CU MN FE NI : > Cu ₅ Zn ₈ -type Al ₈ Cu ₅ (ht) phase
ALER	2 0.5 0.5	

:AL MG:ER :	
AL2ER3	2 0.4 0.6
:AL MG:ER :	
ALER2	2 0.33333 0.66667
:AL MG:ER :	
AL2FE1	2 2 1
:AL CU SI ZN:FE MN NI :	
AL5FE2	2 5 2
:AL CU SI ZN:FE MN NI :	
AL5FE4	
:AL CU FE MN :	
AL13FE4	3 0.6275 0.235 0.1375
:AL CU:FE MN NI ZN:AL SI VA ZN :	
> solution phases based on Al ₁₃ Fe ₄ , aka Al ₃ Fe	
AL4FE	2 4.2 1
:AL:FE :	
ALMG_BETA	2 89 140
:MG LI:AL ZN :	
ALMG_EPS	2 23 30
:MG:AL ZN :	
ALMG_GAMMA	3 5 12 12
:LI MG:AL MG ZN:AL MG ZN :	
ALMGZN_PHI	2 6 5
:MG:AL ZN :	
> a Al-Mg-Zn ternary phase know as PHI	

AL12MN	2 12 1	:AL:MN :
AL6MN	2 6 1	:AL CU ZN:MN FE CU:
AL4MN_R	2 0.81162 0.18838	:AL:MN FE : > AL461MN107
AL4MN_U	2 4 1	:AL ZN:MN :
AL11MN4_LT	2 11 4	:AL ZN:MN FE :
AL11MN4_HT	2 29 10	:AL MN:MN :
AL8MN5	3 12 5 9	:AL ZN:MN:AL MN SI CU :
AL12MO	2 12 1	: AL,SI : MO :
AL5MO	2 5 1	: AL,SI : MO :
AL22MO5	2 22 5	: AL,SI : MO :
AL17MO4	2 17 4	: AL,SI : MO :
AL4MO	2 4 1	: AL,SI : MO :

AL3MO	2 3 1
: AL,SI : MO :	
AL8MO3	2 8 3
: AL,SI : MO :	
AL63MO37	2 .63 .37
: AL,SI : MO :	
ALMO3	2 1 3
: AL,MO,SI : AL,MO :	
AL3NI_D011	2 0.75 0.25
:AL MN NI:FE NI B C :	
AL3NI2	3 3 2 1
:AL SI ZN:AL CU FE MG NI:NI VA :	
AL3NI5	2 0.375 0.625
:AL:NI :	
CA2CU	2 2 1
:CA:CU :	
CACU	2 1 1
:CA:CU :	
HCP_CA	2 1 0.5
:CA:H VA :	
CAH2_LT	2 1 2
:CA:H :	
CAH2_HT	2 1 2
:CA:H :	
CALi2	2 2 1

:LI:CA :			
CA2NI7	2	2	7
:CA:NI :			
CANI3	2	0.25	0.75
:CA:NI :			
CA3SI4	2	0.428571	0.571429
:CA:SI :			
CA14SI19	2	0.424242	0.575758
:CA:SI :			
CASI2	2	0.333333	0.666667
:CA:SI :			
CA3ZN	2	3	1
:CA:ZN :			
CA5ZN3	2	5	3
:CA:ZN :			
CAZN	2	1	1
:CA:ZN :			
CAZN2	2	1	2
:CA:ZN :			
CAZN3	2	1	3
:CA:ZN :			
CAZN11	2	1	11
:CA:ZN :			
CU9ER2	2	9	2
:CU:ER :			

CU7ER2	2 7 2	:CU:ER :
CU5ER_C15B	2 5 1	:CU:ER :
CU2ER	2 2 1	:AL CU:ER :
CUER_B2	2 1 1	:AL CU:ER :
CU9GA4_0	3 6 6 1	:CU:CU GA:GA :
CU9GA4_1	4 6 3 3 1	:CU:CU GA:CU GA:GA :
CU9GA4_2	4 3 3 3 4	:CU:CU VA:CU GA:GA :
CU9GA4_3	3 6 3 4	:CU VA:CU GA:GA :
CUGA2	2 1 2	:CU:GA :
CUGA_THETA	2 0.778 0.222	:CU:GA :
CU5HF	2 5 1	:CU:HF :
CU51HF14	2 51 14	:CU:HF :
CU8HF3	2 8 3	

:CU:HF :					
CU10HF7	2	10	7		
:CU:HF :					
CU1HF2	2	1	2		
:CU:HF :					
CUIN_GAMMA	4	2	2	3	6
:CU:CU IN:CU:CU IN :					
CUIN_THETE	2	0.7	0.3		
:CU:IN :					
CU2IN_HT	3	0.545	0.122	0.333	
:CU:CU IN:IN :					
CU2IN_LT	2	0.64	0.36		
:CU:IN :					
CU11IN9	2	0.55	0.45		
:CU:IN :					
CU37LA3	2	37	3		
:CU:LA :					
CU6LA1_LT	2	6	1		
:CU:LA :					
CU6LA1_HT	2	6	1		
:CU:LA :					
CU5LA1	2	5	1		
:CU:LA :					
CU4LA1	2	4	1		
:CU:LA :					

CU2LA1	2 2 1	:CU:LA :
CU1LA1	2 1 1	:CU:LA :
CUMG2	2 1 2	:CU NI:MG :
CU4SC	2 4 1	:CU:SC :
CU2SC_C11B	2 2 1	:AG CU:SC :
CUSC	2 1 1	:CU:SC :
CU33SI7_DELTA	2 0.825 0.175	:CU ZN:SI :
CU15SI4_EPSILON	2 0.789474 0.210526	:CU MG MN ZN:AL SI :
CU56SI11_GAMMA	2 0.835821 0.164179	:CU MG MN NI SI ZN:SI :
CUSI_ETA	2 0.76 0.24	:CU MN NI ZN:SI :
EPSILON		:CU MN ZN :
FE3ER	2 3 1	:FE:ER :
FE23ER6	2 23 6	

:AL FE:ER :			
FE17ER2	2	17	2
:AL FE:ER :			
MG24R5	2	5	24
:ER MG:AL MG :			
ER5SI3	2	0.625	0.375
:ER:SI :			
ER5SI4	2	0.555556	0.444444
:ER:SI :			
ERSI_OC8	2	0.51	0.49
:ER:SI :			
ERSI_OP8	2	0.5	0.5
:ER:SI :			
ERSI2	2	0.37	0.63
:ER:SI :			
C14_FE2HF	2	0.6667	0.3333
:FE:HF FE :			
C36_FE2HF	2	0.6667	0.3333
:FE:HF :			
C15_FE2HF	2	0.6667	0.3333
:FE:HF :			
FE1HF2	2	0.3333	0.6667
:FE:HF :			
FE2SC_C15	2	0.64	0.36
:FE:SC :			

FE6SC29	2	0.17	0.83
:FE:SC :			
FE2SI	2	2	1
:FE NI:AL SI :			
FESI2_H	2	3	7
:FE NI:AL MG SI :			
FESI2_L	2	1	2
:FE NI:AL SI :			
FESI_B20	2	1	1
:FE MN NI CR:AL MG SI GE :			
> FeSi, MnSi, CrSi, CrGe			
MN5Si3_D88	2	5	3
:CU FE MN NI CR ZR TI:AL CR SI GE SN:			
> Mn5Si3, Cr3Si5, Fe5Si3, Ge3Mn5, Ge3Zr5, Si3Zr5, Sn3Ti5			
GAMMA_D82	4	2	2 3 6
:FE MN ZN:FE MN NI ZN:AL CU FE MN NI SI ZN:AL ZN :			
FEZN_GAMMA1	3	0.137	0.118 0.745
:FE:AL CU FE NI SI ZN:MN ZN :			
FEZN_DELTA	4	5.8E-2	0.18 0.525 0.237
:FE:AL CU FE MN NI SI ZN:ZN:ZN :			
FEZN_ZETA	3	7.2E-2	0.856 7.2E-2
:FE MN NI VA:AL ZN:AL CU SI VA ZN :			
LAH3	3	0.25	0.5 0.25
:LA:H VA:H VA :			
MGH2	2	1	2

:MG:H :	
HFMN	2 0.5 0.5
:HF:MN :	
KNA2	2 1 2
:K:NA :	
KZN13	2 1 13
:K:ZN :	
LA3NI	2 3 1
:LA:NI :	
LA7NI3	2 7 3
:LA:NI :	
LANI	2 1 1
:LA:NI :	
LA2NI3	2 2 3
:LA:NI :	
LA7NI16	2 7 16
:LA:NI :	
LANI3	2 1 3
:LA:NI :	
LA2NI7_LT	2 2 7
:LA:NI :	
LA2NI7_HT	2 2 7
:LA:NI :	
LANI5	2 1 5
:LA:NI :	

LA3SI2	2	0.6	0.4
:LA:SI :			
LA5SI3	2	0.625	0.375
:LA:SI :			
LA5SI4	2	0.5556	0.4444
:LA:SI :			
LASI	2	0.5	0.5
:LA:SI :			
LASI2_A1	2	0.36	0.64
:LA:SI :			
LASI2_A2	2	0.3333	0.6667
:LA:SI :			
LAZN2	2	0.333	0.667
:LA:ZN :			
LAZN4	2	0.2	0.8
:LA:ZN :			
LAZN5	2	0.1667	0.8333
:LA:ZN :			
LA3ZN22	2	0.12	0.88
:LA:ZN :			
LAZN11	2	8.3E-2	0.917
:LA:ZN :			
LAZN13	2	7.1E-2	0.929
:LA:ZN :			
LA2ZN17	2	0.105	0.895

:LA:ZN :	
LI2ZN3_L	2 2 3
:LI:LI ZN :	
LI2ZN3_H	2 2 3
:LI ZN:LI ZN :	
LI2ZN5_L	2 2 5
:LI ZN:ZN :	
LI2ZN5_H	2 2 5
:LI ZN:ZN :	
LIZN4_L	2 1 4
:LI ZN:LI ZN :	
LIZN4_H	2 0.2 0.8
:LI ZN:LI ZN :	
LIZN2	2 1 2
:LI:ZN :	
BCC_B32	2 1 1
:LI ZN:LI ZN :	
MG2NI	2 2 1
:MG ZN:CU NI ZN :	
MG2SI_C1	2 2 1
:MG:GE SI SN :	
> solution phase of Mg2Si, GeMg2, Mg2Sn	
MG7ZN3	2 51 20
:MG:ZN :	
MGZN	2 12 13

:MG:AL CU ZN :	
MG2ZN3	2 2 3
:MG:AL CU ZN :	
L10_TETRA	2 0.5 0.5
:AL CU MN NI TI:AL CU MN NI TI :	
MNNI2	2 1 2
:MN NI:NI :	
MNSC4	2 0.2 0.8
:MN:SC :	
MN11SI19	2 11 19
:MN:AL SI :	
MN3SI	2 3 1
:FE MN NI:AL SI :	
MN6SI	2 17 3
:AL MN:SI ZN :	
MN9SI2	2 33 7
:MN:SI :	
MNZN9	2 0.1 0.9
:MN:ZN :	
MO5SI3	3 0.5 0.125 0.375
: MO : MO SI : AL MO SI :	
MOSI2	2 2 1
: AL SI : MO :	
C40_MOSI2	2 2 1
: AL SI : MO	

C54_MOSI2	2 2 1
: AL SI : MO	
NASI_LT	2 1 1
:NA:SI :	
NASI_HT	2 1 1
:NA:SI :	
NAZN13	2 1 13
:NA:ZN :	
NI5HF	2 0.833 0.167
:NI:HF :	
NI7HF2	2 0.778 0.222
:NI:HF NI :	
NI3HF_LT	2 0.75 0.25
:NI:HF :	
NI3HF_HT	2 0.75 0.25
:NI:HF :	
NI21HF8	2 0.724 0.276
:NI:HF :	
NI7HF3	2 0.7 0.3
:NI:HF :	
NI10HF7	2 0.588 0.412
:NI:HF :	
NI11HF9	2 0.55 0.45
:NI:HF :	
NIHF_LT	2 0.5 0.5

:NI:HF :			
NIHF_HT	2	0.5	0.5
:NI:HF :			
NIHF2	2	1	2
:NI VA:HF :			
HF2SI	2	0.6666667	0.3333333
:HF:SI :			
HF3SI2	2	0.6	0.4
:HF:SI :			
HF5SI3	2	0.625	0.375
:HF:SI :			
HFSI	2	0.5	0.5
:HF:SI :			
HF5SI4	2	0.555556	0.444444
:HF:SI :			
HFSI2	2	0.333333	0.666667
:HF:SI :			
TET_A6P			
:IN SN :			
NI2SI_HT	3	1	1
:CU NI:NI VA:AL SI :			
NI3SI2	2	3	2
:FE NI:SI :			
NI3SI_HT	2	3	1
:FE NI:AL SI :			

L12_FCC	2 1 3	:AL GE NI SI TI V:AL FE ZR NI ZN : > L12 phase, Ni ₃ Si _{rt} , AlZr ₃ , GeNi ₃ , TiZn ₃ , VZn ₃
Ni ₃ Si_MT	2 1 3	:Si:NI :
Ni ₅ Si ₂	2 5 2	:CU FE NI:AL SI :
NiSi_B31	2 1 1	:FE NI:GE SI ZN : > GeNi, NiSi
NiSi ₂	2 2 1	:AL CU SI ZN:CU FE MN NI :
NiZn_LT	2 0.5 0.5	:AL FE MN NI SI ZN:AL FE MG MN NI SI ZN :
NiZn ₈	2 0.1111111 0.8888889	:NI:AL MN ZN :
AlB ₁₂	2 1 12	:AL:B :
Al ₄ C ₃	2 4 3	:AL Si:C :
Al ₅ Cr	2 5 1	:AL Si:CR :
Al ₄ Cr	2 1 4	:CR:AL SI VA :
AlCr_GAMMA1	4 2 2 3 6	

:AL CR SI:CR:AL CR:AL SI :	
GAMMA_D810	3 12 5 9
:AL SI:CR:AL CR SI :	
AL7SR8	2 7 8
:AL:SR :	
AL4M_D13	2 4 1
:AL:CA SR :	
> Al4Ca, Al4Sr	
AL2TI	2 2 1
:AL TI:AL SC TI :	
AL5TI2	2 5 2
:AL TI:AL TI :	
AL5TI3	2 5 3
:AL:TI :	
AL3TI_LT	2 3 1
:AL SI TI:AL SC TI :	
ALTI3_D019	2 3 1
:AL TI:AL SI TI :	
AL21V2	2 21 2
:AL:V :	
AL23V4	2 23 4
:AL:V :	
AL8V5	4 2 2 3 6
:AL V:V:AL V:AL :	
AL4ZR5	2 4 5

:AL:SC ZR :		
AL3ZR2_OF40	2	3 2
:AL LI:SC HF ZR :		
> Al3Zr2, Al3Hf2		
AL2ZR3_TP20	2	2 3
:AL ZN:SC HF ZR :		
> Al2Zr3, Al2Hf3, ZN2Zr3		
AL3ZR_D023	2	3 1
:AL LI:SC HF TI ZR :		
> Al3Zr, Al3Hf		
CU6SN5_HT	3	1 1 1
:CU:CU SN:SN :		
CUSN_GAMMA		
:CU SN :		
CU10SN3		
:CU SN :		
CU3SN	2	3 1
:CU SN:CU SN :		
CU41SN11	2	41 11
:CU SN:CU SN :		
CU6SN5_LT	3	1 1 1
:CU:CU SN:SN :		
CUSR	2	1 1
:SR:CU :		
CU2TI	2	2 1

:CU:TI :	
CU3TI2	2 3 2
:CU:TI :	
CU4TI1	2 4 1
:CU TI:CU TI :	
CU4TI3	2 4 3
:CU:TI :	
CUTI_B11	2 1 1
:CU TI:CU TI :	
CUTI3	2 1 3
:CU TI:TI :	
CU10ZR7	2 10 7
:CU:ZR :	
CU51ZR14	2 51 14
:CU:ZR :	
CU8ZR3	2 8 3
:CU:ZR :	
FE2GE1	3 1 1 1
:FE:FE VA:GE :	
FEGE_ETA	2 13 9
:FE:GE :	
FE6GE5	2 6 5
:FE:GE :	
FE2GE3	2 2 3
:FE:GE :	

FE5SN3_D82	2 5 3
:FE:SN :	
FE3SN2	2 3 2
:FE:SN :	
FEZR3	2 1 3
:FE:ZR :	
MGB4	2 1 4
:MG:B :	
MGB7	2 1 7
:MG:B :	
MG2C3	2 2 3
:MG:C :	
MGC2	2 1 2
:MG:C :	
MG2SR	2 2 1
:MG:SR :	
MG38SR9	2 38 9
:MG:SR :	
MG23SR6	2 23 6
:MG:SR :	
MG17SR2	2 17 2
:MG:SR :	
MN2B_D1F	2 0.6707 0.3293
:MN:B :	
MNB4	2 0.2 0.8

:MN:B :	
M5C2	2 5 2
:MN:C :	
CR3MN5	2 3 5
:CR:MN :	
HIGH_SIGMA	3 8 4 18
:MN:CR:CR MN :	
GEMN3_HT	2 1 3
:GE MN:MN :	
GE2MN3	2 2 3
:GE:MN :	
GE2MN5	2 2 5
:GE MN:MN :	
GE3MN7	2 3 7
:GE:MN :	
MN2SN	2 0.643 0.357
:MN:SN :	
> Mn(2-x)Sn	
MN3SN2	2 3 2
:MN:SN :	
MNTI_LT	2 1 1
:MN:TI :	
MNTI_HT	2 0.515 0.485
:MN:TI :	
MN3TI	2 3 1

:MN:TI :			
MN4TI	2	0.815	0.185
:MN:TI :			
MNV_SIGMA	3	10	4 16
:MN V:V:MN V :			
NI4B3_ORTH	2	0.586	0.414
:NI:B :			
NI4B3_MONO	2	0.564	0.436
:NI:B :			
GENI2	2	0.665	0.335
:NI:GE :			
GE3NI5_HT	2	0.625	0.375
:GE NI:GE NI :			
GE2NI3	2	0.6	0.4
:GE NI:GE :			
GENI3_GAMMA	2	0.744	0.256
:NI:GE :			
GE2NI5	2	0.72	0.28
:NI:GE :			
GE3NI5_LT	2	0.63	0.37
:NI:GE :			
GE12NI19	2	0.613	0.387
:GE NI:GE NI :			
NI7SC2	2	0.222222	0.777778
:SC:NI :			

NISC_B2	2	1	1	
:SC:NI :				
NISC2	2	0.72	0.28	
:SC:NI :				
NI3SN2_LT	3	0.2	0.4	0.4
:SN:NI SN:NI :				
NI3SN_HT	3	0.25	0.25	0.5
:NI SN:NI SN:NI :				
NI3SN2_HT	3	0.33333	0.33334	0.33333
:NI:NI SN:SN :				
NI3SN4	3	0.25	0.25	0.5
:NI:NI SN:SN :				
NISR	2	0.5	0.5	
:NI:SR :				
NI3TI_D024	2	0.75	0.25	
:NI TI:NI TI :				
NITI2	2	1	2	
:NI TI:NI TI :				
NI2V7	2	2	7	
:NI:V :				
NI2V1	2	2	1	
:NI:V :				
NI10ZR7	2	23	17	
:NI:ZR :				
NI21ZR8	2	8	21	

:ZR:NI :			
NI11ZR9	2	11	9
:NI:ZR :			
NI7ZR2	2	7	2
:NI:ZR :			
SC5SI3	2	0.625	0.375
:SC:SI :			
SCSI	2	0.5	0.5
:SC:SI :			
SC3SI5_LT	2	0.375	0.625
:SC:SI :			
SC3SI5_HT	2	0.375	0.625
:SC:SI :			
SCZN	2	0.5	0.5
:SC:ZN :			
SCZN2	2	0.3333	0.6667
:SC:ZN :			
SC13ZN58	2	0.1831	0.8169
:SC:ZN :			
SC3ZN17	2	0.15	0.85
:SC:ZN :			
SCZN12	2	7.7E-2	0.923
:SC:ZN :			
SIB3	3	6	2 6
:B:SI:B SI :			

SIB6	3	210 23 48
:B:SI:B SI :		
SIBX	3	61 1 8
:B:SI:B SI :		
SIC	2	1 1
:C:SI :		
CR3SI	2	3 1
:CR SI:AL CR SI :		
CRSI2_C40	2	1 2
:CR SI V:AL CR SI :		
SI2SR_HT	2	2 1
:SI VA:SR :		
SI2SR_LT	2	2 1
:SI:SR :		
SI3TI5_D88	2	3 5
: SI : TI :		
V3SI	2	0.75 0.25
:V SI:SI V :		
CRZN13	2	1 13
:CR:ZN :		
CRZN17	2	1 17
:CR:ZN :		
SRZN5_LT	2	1 5
:SR:ZN :		
TIZN2	2	1 2

:Ti:ZN :			
TiZN5	2	1	5
:Ti:ZN :			
TiZN10	2	1	10
:Ti:ZN :			
TiZN15	2	1	15
:Ti:ZN :			
V4ZN5	2	4	5
:V:ZN :			
ZN2ZR	2	2	1
:ZN:ZR :			
ZN22ZR	2	22	1
:ZN:ZR :			
ZN39ZR5	2	39	5
:ZN:ZR :			
ZN3ZR_LT	2	3	1
:ZN:ZR :			
ZN3ZR_HT	2	3	1
:ZN:ZR :			
B4C	2	1	1
:B11C B12:B2 C2B CB2 :			
CR2B_ORTH	2	0.666667	0.333333
:CR:B :			
CRB4	2	0.2	0.8
:CR:B :			

SRB6	2 1 6
:SR:B :	
V2B3	2 0.4 0.6
:V:B :	
V5B6	2 0.454545 0.545455
:V:B :	
ZRB12	2 12 1
:B:ZR :	
CU6CE	2 6 1
:CU:CE :	
CU5CE	2 5 1
:AL CU:CE :	
CU4CE	2 4 1
:AL CU:CE :	
CU2CE	2 2 1
:CU:CE :	
CUCE	2 1 1
:CU:CE :	
CE2FE17	2 2 17
:CE:AL FE :	
MGCE	2 1 1
:AL MG:CE :	
MG3CE	2 3 1
:MG:MG CE :	
MG41CE5	2 41 5

:MG:CE :			
MG17CE2	2	17	2
:MG:CE :			
MG12CE	2	12	1
:AL MG:CE :			
CE5SI3	2	3	5
:SI:CE :			
CE3SI2	2	3	2
:CE:SI :			
CE5SI4	2	5	4
:CE:SI :			
CESI	2	1	1
:CE:SI :			
CE3SI4	2	1	1.34
:CE:SI :			
CE3SI5	2	0.37	0.63
:CE:SI :			
CESI2	2	1	2
:CE:AL SI :			
CE7NI3	2	0.7	0.3
:CE:NI :			
CENI	2	0.5	0.5
:CE:NI :			
CENI2	2	0.333333	0.666667
:CE NI:CE NI :			

CENI3	2	0.25	0.75
:CE:AL NI :			
CE2NI7	2	0.222222	0.777778
:CE:AL NI :			
CENI5	2	0.166667	0.833333
:ER CE NI:AL CE CU NI :			
CR3C2	2	3	2
:CR:C :			
V3C2	2	3	2
:V:C :			
CDCU2	2	1	2
:CD:CU :			
CD3CU4	2	0.4286	0.5714
:CD:CU :			
CD8CU5	4	2	3 2 6
:CU:CD CU:CU:CU CD :			
CD10CU3	2	0.7692	0.2308
:CD:CU :			
SN_HP1			
:CD IN SN :			
CR3GE	2	0.75	0.25
:CR GE:CR GE :			
CR5GE3_HT	2	0.625	0.375
:CR GE:GE CR :			
CR5GE3_LT	2	0.625	0.375

:CR GE:GE CR :			
CR11GE19	2	0.367	0.633
:CR:GE :			
GE2SR	2	2	1
:GE:SR :			
GE3TI5	2	5	3
:TI:GE :			
V3GE	2	0.75	0.25
:V:GE :			
V17GE31	2	0.354	0.646
:V:GE :			
SR3SN5	2	0.375	0.625
:SR:SN :			
SRSN3	2	0.25	0.75
:SR:SN :			
SRSN4	2	0.2	0.8
:SR:SN :			
SN3TI2	2	3	2
:SN:TI :			
V3SN	2	0.205	0.795
:SN:V :			
VSN2	2	0.6	0.4
:SN:V :			
SN3ZR5	3	5	3
:ZR:SN:SN VA :			

> aka eta		
SNZR3_A15	2	3 1
:SN ZR:SN ZR :		
V2ZR	2	2 1
:V:ZR :		
AL14CA13	2	14 13
:AL MG ZN:CA :		
AL3CA8	2	3 8
:AL:CA MG :		
AL4CE	2	0.8 0.2
:AL:CE :		
AL11CE3	2	0.7857 0.2143
:AL MG:CE :		
AL3CE_H	2	0.75 0.25
:AL:CE :		
AL3CE_L	2	0.75 0.25
:AL SI:CE :		
ALCE	2	0.5 0.5
:AL:CE :		
ALCE2	2	0.3333 0.6667
:AL:CE :		
ALCE3_H	2	0.25 0.75
:AL:CE :		
ALCE3_L	2	0.25 0.75
:AL:CE :		

AL13CO4	2 13 4
:AL:CO :	
AL3CO	2 3 1
:AL:CO :	
AL5CO2	2 5 2
:AL:CO :	
AL9CO2	2 9 2
:AL:CO :	
AL3LA	2 3 1
:AL:LA :	
ALLA	2 1 1
:AL:LA :	
AL53LA22	2 0.707 0.293
:AL:LA :	
AL11LA3_LT	2 11 3
:AL:LA :	
AL11LA3_HT	2 11 3
:AL:LA :	
AL2LI3	2 2 3
:AL MG:LI :	
ALLI2	2 1 2
:AL:LI :	
AL4LI9	2 4 9
:AL:LI :	
B32_ALLI	2 1 1

:AL LI MG:LI MG VA :	
AL3X	2 1 3
:ER LI SC TI ZR:AL MG :	
> Al3Sc (dissolving Ti, Zr), Al3Li	
AL2SC	2 1 2
:SC TI ZR:AL :	
ALSC	2 1 1
:SC ZR:AL :	
AL3HF4	2 3 4
:AL:HF :	
LI22SI5	2 22 5
:LI:SI :	
LI13SI4	2 13 4
:LI:SI :	
LI7SI3	2 7 3
:LI:SI :	
LI12SI7	2 12 7
:LI:SI :	
AG9CA2	2 0.818182 0.181818
:AG:CA :	
AG7CA2	2 0.777778 0.222222
:AG:CA :	
AG2CA	2 0.666667 0.333333
:AG:CA :	
AGCA3	2 0.25 0.75

:AG:CA :				
AG4SC	2	0.8	0.2	
:AG:SC :				
AGSC	2	0.5	0.5	
:AG:SC :				
AL4C4SI	3	4	1	4
:AL:SI:C :				
AL8C7SI	3	8	1	7
:AL:SI:C :				
AL20CECR2	3	0.869565	4.3478E-2	8.6957E-2
:AL:CE:CR :				
AL8CEM4	3	0.6154	7.69E-2	0.3077
:AL:CE ER:AL CR CU FE MN :				
> T1				
AL10CE2M7	2	0.8947	0.1053	
:AL CR CU FE MN:CE ER :				
> T2				
AL3CECU	2	0.8	0.2	
:AL CU:CE :				
> T3				
ALCEM	3	0.3333	0.3333	0.3334
:AL:CE ER:CU NI :				
> T4				
ALCE2CU2	3	0.2	0.4	0.4
:AL:CE:CU :				

> T5		
ALCEFE	2 2 1	
:AL:FE:CE :		
AL10CEFE2	3 10 1 2	
:AL:CE:ER:FE :		
AL8CEFE2	3 8 1 2	
:AL:CE:FE :		
AL13CEMG6	3 0.667 5E-2 0.283	
:AL:CE:MG :		
AL2CENI	3 2 1 1	
:AL:CE:NI :		
> T2		
AL5CE2NI5	3 0.35 0.165 0.485	
:AL:CE:NI :		
> T3, 13		
AL4CENI	3 4 1 1	
:AL:CE:NI :		
> T5		
AL5CE1NI2	3 5 1 2	
:AL:CE:NI :		
> T6		
AL23CE4NI6	3 23 4 6	
:AL:CE:NI :		
> T8		
AL60CE12NI28	3 0.6 0.12 0.28	

:AL:CE:NI :			
> T11			
AL40CE30NI30	3	0.403	0.304 0.293
:AL:CE:NI :			
> T12			
ALCESI	2	2	1
:AL SI:CE :			
AL7CE5SI3	3	0.49	0.333333 0.176667
:AL:CE:SI :			
ALCESI2	3	1	1 2
:AL:CE:SI :			
AL4CE3SI6	3	4	3 6
:AL:CE:SI :			
AL13CR4SI4	3	13	4 4
:AL:CR:SI :			
> Al-Cr-Si, tao 1			
AL9CR3SI	3	9	3 1
:AL:CR:SI :			
> Al-Cr-Si, tao 2			
ALCRSI_T3	2	11	4
:AL SI:CR :			
> Al-Cr-Si, tao 3			
ALCRSI_T4	3	58	31.5 10.5
:AL:CR:SI :			
> Al-Cr-Si, tao 4, AL58CR32SI11			

AL9CU6ER5	3	0.45 0.3 0.25
:AL:CU:ER :		
AL5CU3ER2	3	0.5 0.3 0.2
:AL:CU:ER :		
AL3CU1ER1	3	0.6 0.2 0.2
:AL:CU:ER :		
AL62CU25FE13	3	0.125 0.255 0.62
:FE:AL CU:AL :		
AL7CU2FE	3	1 2 7
:FE NI:CU:AL :		
> Solution phase of the ternary compound Al ₇ Cu ₂ Fe		
AL10CU10FE	3	1 10 10
:FE:AL CU:AL :		
AL2CULI	3	0.5 0.25 0.25
:AL:CU:LI :		
> Al-Cu-Li ternary phase, i.e. T1		
ALCULI_T2	3	0.57 0.11 0.32
:AL:CU:LI :		
> Al-Cu-Li ternary phase, T2		
ALCULI_R	3	0.55 0.117 0.333
:AL:CU:LI :		
> Al-Cu-Li ternary phase, R		
ALCULI_B	3	0.6 0.32 8E-2
:AL:CU:LI :		
> Al-Cu-Li ternary phase, TB		

Q_PHASE	3 7 3 6	
:AL:CU:Mg :		
> Al ₇ Cu ₃ Mg ₆ , Al-Cu-Mg ternary phase		
S_PHASE	3 2 1 1	
:AL SI:CU:Mg :		
> also known as Al ₂ CuMg or S		
S_PRIME	3 2 1 1	
:AL:CU:Mg :		
> slightly distorted S_phase which forms during aging precipitation. Strain and interfacial energy needs to be added		
S_DPRIME	3 5 5 2	
: AL : CU : Mg :		
> metastable precipitate, related to S_PHASE		
T_PHASE	4 26 6 48 1	
:Mg:AL Mg:AL CU MG Zn:AL :		
> Solution (Al,Cu,Zn) ₄₉ Mg ₃₂ , stable in Al-Mg-Zn, Al-Cu-Mg, Al-Cu-Mg-Zn		
AL ₂₈ CU ₄ MN ₇	3 28 7 4	
:AL:Mn:CU :		
AL ₁₁ CU ₅ MN ₃	3 11 3 5	
:AL:Mn:CU :		
ALCU ₃ MN ₂	3 1 2 3	
:AL:Mn:CU :		
AL ₇ CU ₄ NI	2 1 1	
:AL:FE CU NI VA :		
ALCUSC_TAU	3 0.6154 0.3077 7.69E-2	
:AL CU:AL CU:SC :		

AL6ER2FE11	3 6 2 11
:AL:ER:FE :	
AL7ERMG2	3 0.66667 0.1 0.23333
:AL:ER:MG :	
AL9FENI	2 9 2
:AL:FE NI :	
AL10FE3NI	2 5 2
:AL:FE NI :	
AL71FE5NI24	3 0.71 5E-2 0.24
:AL:FE:NI :	
ALFESI_T1	2 5 3
:AL SI:FE :	
> Al-Fe-Si ternary phase, tao 1 / tao 9	
ALFESI_T2	4 0.5 0.2 0.1 0.2
:AL:FE:SI:AL SI :	
> Al-Fe-Si ternary phase, tao 2, gamma_AlFeSi	
ALFESI_T3	3 0.56 0.24 0.2
:AL:FE:SI :	
> Al-Fe-Si ternary phase, AL56FE24SI10, tao 3	
ALFESI_T4	4 0.4166 0.1667 0.25 0.1667
:AL:FE:SI:AL SI :	
> Al-Fe-Si ternary phase, tao 4, delta_AlFeSi	
AL8FE2SI	4 0.6612 0.19 4.96E-2 9.92E-2
:AL:FE:SI:AL SI :	
> solution of the Al-Fe-Si ternary phase, tao 5, alpha_AlFeSi	

AL9FE2SI2	4	0.598 0.152 0.1 0.15
:AL:FE:SI:AL SI :		
> Al-Fe-Si ternary phase, tao 6, aka Al ₅ FeSi, beta_AlFeSi		
ALFESI_T7	2	3 1
:AL SI:FE :		
> Al-Fe-Si ternary phase, AL9FE5SI6, tao 7		
ALFESI_T8	2	2 1
:AL SI:FE :		
> Al-Fe-Si ternary phase, AL2FE3SI4, tao 8		
ALFESI_T10	3	0.6 0.25 0.15
:AL:FE:SI :		
> Al-Fe-Si ternary phase, AL60FE25SI15, tao 10		
ALFESI_T11	3	0.65 0.25 0.1
:AL:FE:SI :		
> Al-Fe-Si ternary phase, AL85FE30SI15, tao 11		
ALFEZN_GAMMA	2	0.255 0.745
:AL FE ZN:ZN :		
> Al-Fe-Zn ternary phase, aka gamma 2, no detailed structure		
ALLIMG_T	3	0.53 0.33 0.14
:AL:LI:MG :		
ALLISI	3	0.333333 0.333333 0.333334
:LI:AL:SI :		
AL3LI8SI5	3	0.5 0.1875 0.3125
:LI:AL:SI :		
ALLI5SI2	3	0.6625 8.75E-2 0.25

:LI:AL:SI :	
ALLI2ZR	3 1 2 1
:AL:LI:ZR :	
AL18MG3MN2	3 18 3 2
:AL:MG:MN :	
ALMG3NI2	3 1 2 3
:AL:NI:MG :	
> Ternary phase AlMg ₃ Ni ₂ , cF96, Fd-3m, Ti ₂ Ni type	
BETA_PRIME	2 1.8 1
:MG:SI :	
> metastable precipitate, Mg ₉ Si ₅ /Mg _{1.8} Si, related to Mg ₂ Si	
B_PRIME	3 3 9 7
:AL:MG:SI :	
> metastable precipitate, B_Prime, Al-containing Pre-beta phase	
U1_AL2MGSI2	3 2 1 2
:AL:MG:SI :	
> metastable precipitate, U1_Al ₂ MgSi ₂ , Al-containing Pre-beta phase	
U2_AL4MG4SI4	3 1 1 1
:AL:MG:SI :	
> metastable precipitate, U2_Al ₄ Mg ₄ Si ₄ , Al-containing Pre-beta phase	
BETA_DPRIME	3 2 5 4
:AL SI:MG:SI :	
> metastable beta double prime, related to Mg ₂ Si, Mg ₅ Si ₆ , Al ₂ Mg ₅ Si ₄	
ETA_PRIME	3 0.21 0.28 0.51
: AL : MG : CU,ZN :	

> metastable precipitate, related to MgZn ₂ -based Eta phase			
T_PRIME	3	0.3 0.45 0.25	
:AL:Mg:ZN :			
> metastable precipitate, related to T_PHASE			
AL31MN6NI2	3	31 6 2	
:AL:Mn:NI :			
> Orthorhombic, ternary Al-Mn-Ni phase			
AL2MN2SI3	3	2 2 3	
:AL:Mn:Si :			
> the Al-Mn-Si ternary phase, tao1			
AL5MN6SI7	3	5 6 7	
:AL:Mn:Si :			
> the Al-Mn-Si ternary phase, tao2			
AL1MN1SI1	3	1 1 1	
:AL:Mn:Si :			
> the Al-Mn-Si ternary phase, tao3			
AL3MNSI2	3	3 1 2	
:AL:Mn:Si :			
> the Al-Mn-Si ternary phase, tao4			
AL3MN4SI2	3	3 4 2	
:AL:Mn:Si :			
> the Al-Mn-Si ternary phase, tao5			
ALMNSI_T6	2	4 1	
:AL MN:Si :			
> the Al-Mn-Si ternary phase, tao6			

ALMNSI_T8	4 6 3 3 1
:AL:MN:AL MN SI:AL SI :	
> the Al-Mn-Si ternary phase, tao 8	
AL15SI2M4	4 16 4 1 2
:AL:FE MN:SI:AL SI :	
> Solution of Al-Mn-Si ternary phase, tao 9, Al ₁₅ (Mn,Fe) ₃ Si ₂	
AL2MNSI3	3 2 1 3
:AL:MN:SI :	
> the Al-Mn-Si ternary phase, tao10	
AL24MN5ZN	3 5 1 24
:MN ZN:ZN:AL :	
AL9MN2ZN	3 2 1 9
:MN:ZN:AL :	
AL11MN3ZN2	3 3 2 11
:MN:ZN:AL :	
ALNI2SI	2 1 1
:AL SI VA:NI :	
AL6NI3SI	3 6 3 1
:AL:NI:SI :	
ALNI16SI9	3 1 16 9
:AL:NI:SI :	
ALNI2ZN	3 0.25 0.5 0.25
:AL:NI:ZN :	
AL13NI38ZN49	3 0.13 0.38 0.49
:AL:NI:ZN :	

> Al-Ni-Zn ternary phase		
ALSC2SI2	3	1 2 2
:AL:SC:SI :		
ALSI3TI2	3	0.2 0.466667 0.333333
:AL SI:SI:TI :		
ALSI7TI4	3	0.1 0.566667 0.333333
:AL SI:SI:TI :		
CULIMG_T	3	1 8E-2 1.92
:CU:LI:MG :		
CU16MG6SI7	3	16 6 7
:CU:MG:SI :		
CU3MG2SI	3	2.74 2 1.26
:CU:MG:SI :		
CU5MN4SI	3	0.5 0.37 0.13
:CU:MN:SI :		
CUMNZN	3	0.334 0.333 0.333
:CU:MN:ZN :		
CU6NISI3	2	0.732 0.268
:CU NI:SI :		
CU46NI25SI29	3	0.458 0.25 0.292
:CU:NI:SI :		
FE5NI3SI2	2	4 1
:FE NI:SI :		
ZN13M2	2	1 6.5
:FE NI:ZN :		

MG6MN3NI	3	0.5	0.1666667	0.3333333
:MG:MN:NI :				
MGNI6SI6	3	1	6	6
:MG:NI:SI :				
MG2NI3SI	3	2	3	1
:MG:NI:SI :				
MG10NI55SI35	3	2	11	7
:MG:NI:SI :				
MG2NI16SI11	3	1	8	5.5
:MG:NI:SI :				
MG5NI9SI	3	1	1.8	0.2
:MG:NI:SI :				
MG9NI29SI16	3	9	29	16
:MG:NI:SI :				
MGNI6ZN6	4	3	4	1 2
:MG ZN:MG NI ZN:NI:ZN :				
MN15NI45SI40	3	0.15	0.45	0.4
:MN:NI:SI :				
> Mn-Ni-Si ternary phase, T1 or N				
MN15NI50SI35	3	0.15	0.5	0.35
:MN:NI:SI :				
> Mn-Ni-Si ternary phase, T2 or PHI				
MN6NI16SI7	3	0.206897	0.551724	0.241379
:MN:NI:SI :				
> Mn-Ni-Si ternary phase, T3 or G				

MN1NI1SI1	3 1 1 1
:MN:NI:SI :	
> Mn-Ni-Si ternary phase, T4 or E	
MNNISI_T5	2 1 2
:MN:NI SI :	
> Mn-Ni-Si ternary phase, T5 or "tao 1"	
MNNISI_T6	2 1 2
:MN:NI SI :	
> Mn-Ni-Si ternary phase, T6 or "tao 2"	
MN3NI2SI	3 3 2 1
:MN:NI:SI :	
> Mn-Ni-Si ternary phase, T7 or Omega	
MN2NISI	2 3 1
:MN NI:SI :	
> Mn-Ni-Si ternary phase, T8 or S	
MN6NISI3	3 0.61 0.12 0.27
:MN:NI:SI :	
> Mn-Ni-Si ternary phase, T9 or R	
MN66NI4SI30	3 0.66 4E-2 0.3
:MN:NI:SI :	
> Mn-Ni-Si ternary phase, T10 or U	
MN52NI29SI19	3 0.52 0.29 0.19
:MN:NI:SI :	
> Mn-Ni-Si ternary phase, T11 or W	
MN7NI7ZN86	3 7E-2 7E-2 0.86

:MN:NI:ZN :				
NI2SiZN_T1	3	0.5	0.25	0.25
:NI:SI:ZN :				
NI9Si2ZN_T2	3	0.75	0.1675	8.25E-2
:NI:SI:ZN :				
NI2SiZN3_T3	3	2	1	3
:NI:SI:ZN :				
NiSiZN_T4	3	3	2	1
:NI:SI:ZN :				
> Ni-Si-Zn tao 4, Ni3Si2Zn1				
Q_ALCUMGSI	4	5	2	8 6
:AL:CU:MG:SI :				
> Quaternary phase, aka Q, Al5Cu2Mg8Si6, Al3Cu2Mg9Si7 & Al4Cu2Mg8Si7				
AL18Fe2MG7Si10	4	18	2	7 10
:AL:FE:MG:SI :				
> Quaternary phase, aka Al8FeMg3Si6 and Q_/PHI/H_PHASE				